

Industrial Fluid Solutions

Market segment
Industrial Hose

Contact
Continental
703 S. Cleveland Massillon Road
Fairlawn, OH 44333-3023 U.S.A.
1-800-235-8872
www.continental-industry.com

Your local contact
www.contitech.de/contactlocator

Canada
1-800-263-7788

Continental
The Future in Motion

The content of this publication is not legally binding and is provided as information only. The trademarks displayed in this publication are the property of Continental AG and/or its affiliates. Copyright © 2019 ContiTech AG. All rights reserved. For complete information go to: www.contitech.de/dscl_en

21087740 INH-CO-BR-CSMN-19

Continental
The Future in Motion



Industrial Hose Assembly Manual

www.continental-industry.com

Table of Contents

NAHAD Crimp Procedures	3	Dixon Part Numbers - Sanitary Style Crimp Stems	32
Crimp Procedure with Dixon Sanitary Style Crimp Stems	4	Table F-A - 1.0" Hose Crimp Chart.....	33
Crimp Solutions by Application	5-8	Table F-A - 1.5" Hose Crimp Chart.....	34
Air	5	Table F-A - 2.0" Hose Crimp Chart.....	35
Beverage	5	Table F-A - 2.5" Hose Crimp Chart.....	36
Chemical	6	Table F-A - 3.0" Hose Crimp Chart.....	37
Cleaning Equipment	6	Table F-B - 3.0" Hose Crimp Chart.....	38
Food	6	Table F-C - 1.0" Hose Crimp Chart.....	39
Material Handling Bulk	7	Table F-C - 1.5" Hose Crimp Chart.....	40
Petroleum Bulk Transfer	7	Table F-C - 2.0" Hose Crimp Chart	41
Steam	8	Table F-C - 2.5" Hose Crimp Chart	42
Vacuum	8	Table F-C - 3.0" Hose Crimp Chart	43
Water Discharge.....	8	Table F-D - 2.0" Hose Crimp Chart	44
Water S&D.....	8	Vintner Reserve 2.0" and 3.0"	45-46
Chart A - Insta-Lock™ Crimp Dimensions	9-19	Appendix	
Chart B - Paladin®/Insta-Lock™ Crimp Dimensions ...	20-22	Assembly Instructions for Hose With	
Chart C - Pressure Washer Hose Crimp Dimensions ...	23-24	PVC Helix in the Cover	48
Chart D - Air & Multipurpose Hose Crimp Dimensions ...	25-27	Instructions for Replacing Handles, Pins	
Chart E - Steam Hose Crimp Dimensions	28	and Rings on Insta-Lock™ Fittings	48
Chart F - DEF Dispensing Hose Crimp Dimensions	28	Hose Testing Methods	49-50
Chart G - Hydrocarbon Drain Hose Crimp Dimensions ...	28	Electrical Resistance Tests for	
Chart H - Velocity® Water S&D Hose Crimp Dimensions ...	29-31	Hose and Hose Assemblies	51-53
		Velocity® Crimp Instructions	54
		ARPM Hose Care Inspection Procedures	55-57
		Notes	58

Crimp Procedures

Crimp Fabrication Procedures reprinted with permission from the National Association of Hose and Accessories Distributors (NAHAD) Hose Assembly Guidelines™ in compliance with all stated conditions and terms of use.

Fabrication Procedures:

1. Cut hose end square and clean any debris from tube interior.
2. Bend grounding wire inside of hose, extending wire approximately 1/2 in. (12.7mm).
3. Measure the outer diameter of the hose, preferably with a pi tape.
4. Based on the hose outer diameter, select the proper ferrule. Mark a line on the hose cover at the distance from the end of the hose that equals the insertion depth. This becomes a visual check to determine if the hose is fully bottomed into the fitting.
5. Slide the ferrule over the stem collar. If the ferrule has flats, be sure they line up with the flats on the hose collar.
6. Lubrication should only be used if necessary.
7. Insert the stem into the hose squarely without causing damage to the tube.
8. Select the desired crimp length and crimp OD using manufacturer's recommendations.
9. Based on #8, select the proper die set using the crimp machine manufacturer's recommendations.
10. Place the hose assembly in the die opening.
11. Jog the crimp dies until they just contact the ferrule. Be sure the ferrule and crimp dies are lined up properly to achieve the desired crimp length.
12. Crimp the ferrule to the desired diameter.
13. Retract the dies and remove the hose assembly.
14. Measure the crimp diameter to ensure it meets manufacturer's specifications.
15. If the OD is too large, re-crimp the ferrule until it meets the required specification. If the crimp diameter is too small, consult the coupling manufacturer.
16. Repeat steps 1 through 15 for the other end.


Testing:

Hydrostatic testing as required.
Conductivity test required.

Crimp procedure with Dixon Sanitary Style Crimp Stems

1. Cut hose to length required and ensure that the end is squared off. The coupling components and the hose bore must be clean and free of contaminants. If hose is cut with a saw, it is important to blow out any cutting residue with a reverse air jet—ensure all safety protection is worn. Cutting hose with a knife method helps keep the hose bore clean.
2. Hoses with antistatic or helix wires have the possibility to be made as an "electrically continuous assembly," so check the customer's requirement whether it needs to be terminated onto the coupling. Follow standard NAHAD procedure for wire termination.
3. Measure the hose OD with a pi tape or measure the hose wall at 4 positions with a caliper. Hoses with helix wire are considered to have a fixed hose ID, whereas hose without it are more subject to ID change from handling and process. The preferred method for softwall hose is wall measurement with a caliper.
4. Refer to the appropriate chart for final crimp OD.
5. Insert the ferrule over the hose. DO NOT insert the ferrule all the way; leave a gap of about 3/16" to 1/4" inside the ferrule for material flow. Then pencil mark the final position of the ferrule on the hose cover. Note: rubber is not compressible and will need a place to flow.
6. Lubricate the hose ID and the stem with a soapy solution from a spray bottle (5% solution of dish soap).
7. Push the stem into the hose while maintaining the ferrule in its final position. Make sure the stem is positioned to lock with the ferrule.
8. Dial the crimp diameter.
9. Position the stem and ferrule into the crimping machine, close the dies to lightly grip the ferrule, validate the stem/ferrule interlocking position. Make sure the hose is aligned with the coupling, then crimp the ferrule.
10. Remove hose end from the crimper, measure the OD over the ferrule and compare with the chart. If needed, make adjustment.

Note: Hose with plastic helices tend to shrink after cooling. It is normal to have to use a hose pusher to insert the stem into the hose.

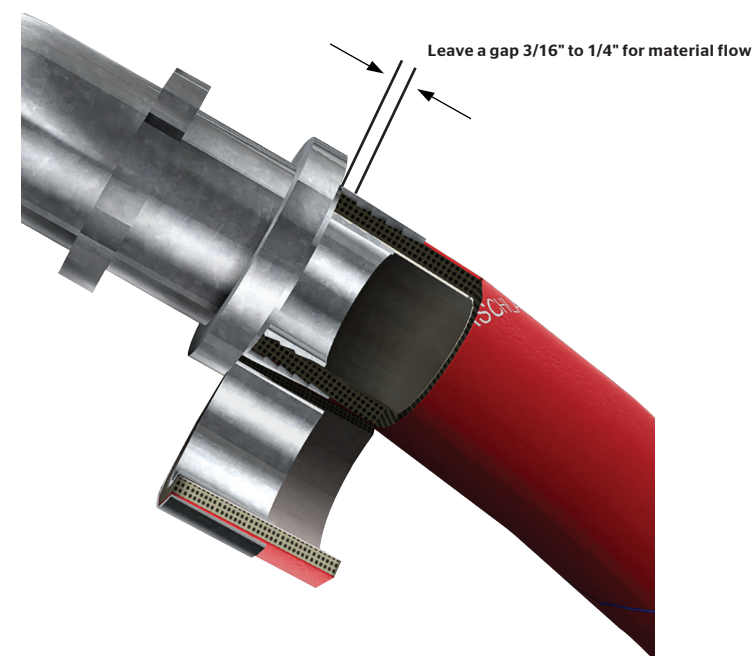

Crimp Solutions by Application

A = Chart A B = Chart B C = Chart C D = Chart D
 E = Chart E F = Chart F G = Chart G
 - = Not available or not applicable

Air

	3/16"	1/4"	3/8"	1/2"	5/8"	3/4"	1"	1 1/4"	1 1/2"	2"
Frontier 200	D	D	D	D	D	D	D	D	D	D
Frontier 250	D	D	D	D	D	D	D	D	D	D
Frontier 300	D	D	D	D	D	D	D	D	D	D
Ortac® 250	D	D	D	D	D	D	D	D	D	D
Ortac® 300	D	D	D	D	D	D	D	D	D	D
Variflex™ 200	D	D	D	D	D	D	D	D	D	D
Variflex™ 300	D	D	D	D	D	D	D	D	D	D
Gorilla®	D	D	D	D	D	D	D	D	D	D
Mine Spray	-	-	-	-	-	D	D	D	D	-
Super Ortac®	-	-	-	-	-	D	D	D	D	-
Prospector™ Air	D	-	-	-	-	-	D	-	-	-
Prospector™ Plus Air	D	-	-	-	-	-	D	-	-	-

Beverage

	1"	1 1/2"	2.0"	2 1/2"	3.0"
Drinkline		F-A	F-A		F-B
ExtremeFlex™ Beverage	F-A	F-A	F-A	F-A	F-A
ExtremeFlex™ Beverage EZ Clean	F-C	F-C	F-C		F-C
ExtremeFlex™ Food	F-A	F-A	F-A	F-A	F-A
EZ Glide Wine			F-D		
Gray Flextra		F-A	F-A	F-A	F-A
Gray Food	F-A	F-A	F-A	F-A	F-A
Purple Snake	F-A	F-A	F-A		F-A
Vintner™ Reserve	F-A	F-A	F-A		F-A
White Flextra		F-A	F-A	F-A	F-A
White Flexwing®	F-A	F-A	F-A	F-A	F-A
White Softwall	F-A	F-A	F-A	F-A	F-A

Note: Always use the latest edition of the crimp chart.

Crimp Solutions by Application

A = Chart A B = Chart B C = Chart C D = Chart D
 E = Chart E F = Chart F G = Chart G
 - = Not available or not applicable

Chemical

	1/2"	5/8"	3/4"	1"	1 1/4"	1 1/2"	2"	2 1/2"	3"	4"
ExtremeFlex™ Brown	-	-	-	A	A	A	A	-	A	A
ExtremeFlex™ Purple	-	-	-	-	-	A	A	-	A	A
Chem One™	-	-	-	A	-	A	A	A	A	-
Hi-Per®	A	-	A	A	A	A	A	A	A	A
Viper™	-	-	-	A	-	A	A	A	A	A
Fabchem™	A	-	A	A	A	A	A	A	A	A
Blue Flexwing®	A	-	A	A	A	A	A	A	A	A
Green XLPE	A	-	A	A	A	A	A	A	A	A
Brown Flexwing®	A	-	A	A	A	A	A	A	A	A
Purple Flexwing®	A	-	-	A	-	A	A	-	A	A
Orange Flexwing®	-	-	A	A	A	A	A	A	A	A
DEF Transfer Hose	A	-	A	A	A	A	A	A	A	A
DEF Dispensing Hose	-	-	F	-	-	-	-	-	-	-
Hydrocarbon Drain Hose	-	-	G	-	-	-	-	-	-	-
Infinity™	-	-	-	-	-	-	B	-	B	B

Cleaning Equipment

	1/4"	3/8"	1/2"	5/8"	3/4"	1/4"	3/8"	1/2"	5/8"	3/4"	
Neptune™	C	C	C	-	-	Galvanator®	-	C	C	-	-
Gauntlet®	C	C	C	-	-	Whitewater®	-	C	C	-	-
Fortress®	-	C	-	-	-	SpiraFlow®	-	C	-	-	-

Food

	3/4"	1"	1 1/4"	1 1/2"	2"	2 1/2"	3"	4"
ExtremeFlex™ Food Grade Gray	-	-	-	-	A	A	A	A
ExtremeFlex™ Food Grade White	-	-	-	-	A	A	A	A
White Flexwing®	A	A	A	A	A	A	A	A
Plicord® Gray Food	A	A	A	A	A	A	A	A
White Flextra®	-	-	-	A	A	A	A	A
White Softwall	-	A	A	A	A	A	A	A
Exstatic®	-	-	-	-	A	-	A	A
Harvest™	-	-	-	-	A	-	A	A
Potable Water Discharge	A	A	A	A	A	A	A	A
Vintner™	-	A	A	A	A	A	A	-
Pyroflex® III	-	-	-	A	A	A	A	A
ExtremeFlex™ Beverage	-	-	-	A	A	A	A	A

Crimp Solutions by Application

A = Chart A B = Chart B C = Chart C D = Chart D
 E = Chart E F = Chart F G = Chart G
 - = Not available or not applicable

Material Handling Bulk

	1/2"	5/8"	3/4"	1"	1 1/4"	1 1/2"	2"	2 1/2"	3"	4"	6"
Black Softwall	-	-	-	-	-	-	A	A	A	A	A
Plicord® Torridair™	A	-	-	-	A	A	A	A	A	A	A
Pyroflex® II Hot Air	-	-	-	-	-	-	A	-	A	A	A
Flextra® Dry Material (75 psi)	-	-	-	-	-	-	A	A	A	A	A
Tan Flextra® (75 psi)	-	-	-	-	-	A	A	A	A	A	A
Tan Softwall (75 psi)	A	-	A	-	-	-	A	A	A	A	A

Petroleum Bulk Transfer

	1/2"	5/8"	3/4"	1"	1 1/4"	1 1/2"	2"	2 1/2"	3"	4"	6"
Arctic® ExtremeFlex™ Blue	-	-	-	-	-	-	A	-	A	A	-
Arctic® ExtremeFlex™ Black	-	-	-	-	-	-	A	-	A	A	-
Plicord® ExtremeFlex™	A	-	A	A	A	A	A	A	A	A	A
Flexwing® VersaFuel™	A	-	A	A	A	A	A	A	A	A	A
Plicord® Flexwing® Petroleum	A	-	A	A	A	A	A	A	A	A	A
Red Flextra® 150	-	-	-	-	-	-	A	-	A	A	-
Red Flextra® 100	-	-	-	-	-	A	A	A	A	A	-
Plicord® LW Black Flextra™ II	-	-	-	-	-	-	A	A	A	A	-
Infinity™/Paladin® Drop	-	-	-	-	-	-	B	-	B	B	-
Plicord® Fuel Discharge	-	-	A	A	A	A	A	A	A	A	A
Plicord® Arctic Flexwing®	-	-	-	A	A	A	A	A	A	A	-
Prospector™ Oilfield 150	-	-	A	A	A	A	A	A	A	A	A
Prospector™ Oilfield 300	-	-	A	A	A	A	A	A	A	A	A
Prospector™ Flex Oilfield	-	-	-	A	A	A	A	A	A	A	-
Plicord® Super Black Flexwing®	-	-	A	A	A	A	A	A	A	A	A

Crimp Solutions by Application

A = Chart A B = Chart B C = Chart C D = Chart D
 E = Chart E F = Chart F G = Chart G
 - = Not available or not applicable

Steam

	1/2"	3/4"	1"	1 1/4"	1 1/2"	2"
Flexsteel® 250 Steam Black	E	E	E	-	-	E
Flexsteel® 250 Steam Red	-	E	E	-	-	E
Flexsteel® 250 CB Extreme	-	E	-	-	-	-
Flexsteel® 250 ORS Steam	-	E	-	-	-	-

Vacuum

	1/4"	3/8"	1/2"	5/8"	3/4"	1"	1 1/4"	1 1/2"	2"	2 1/2"	3"	4"
Plicord® LW Vacuum	-	-	-	-	-	-	A	A	A	A	A	A
Plicord® HD Vacuum	-	-	-	-	-	A	A	-	-	A	A	A
Plicord® HD Ind. Vacuum	-	-	-	-	-	-	-	-	A	A	A	A

Water Discharge

	1"	1 1/4"	1 1/2"	2"	2 1/2"	3"	4"	6"
Plicord® Versiflo™ 125 Discharge	-	-	-	-	-	-	-	A
Plicord® Water Discharge 150	A	A	A	A	A	A	A	A
Plicord® HD Water Discharge	A	A	A	A	A	A	A	A
Potable Water	A	A	A	A	A	A	A	-
Jetting & Utility	A	-	A	A	A	A	A	-
Plicord® Furnace Door	-	-	-	-	-	-	-	-

Water S&D

	1"	1 1/4"	1 1/2"	2"	2 1/2"	3"	4"	6"	8"
Flexwing® Water S&D	A	A	A	A	A	A	A	A	-
Versiflo™ 150 Water S&D	A	A	A	A	A	A	A	A	-
Plicord® Con-Ag™ Water S&D	A	A	A	A	A	A	A	A	-
Velocity® Water S&D	-	-	H	H	-	H	H	H	H

1/2 in. Chart A | Insta-Lock™

Insta-Lock™ 1/2 in. Crimp Chart*

Measured Hose OD, Decimal Min. / Max.	Measured Hose OD In Closest 64ths	Ferrule ID	Finished Crimp Diameter Inches	Finished Crimp Diameter Closest 64ths	Insta-Lock™ Ferrule Part #	Perma-Crimp™	
						Die Set**	Approximate Setting
0.846 / 0.858	54/64	60/64	0.89	57/64	FRSSO50060	19	3.61
0.859 / 0.870	55/64	60/64	0.90	58/64	FRSSO50060	19	3.86
0.871 / 0.882	56/64	60/64	0.91	58/64	FRSSO50060	19	4.11
0.883 / 0.894	57/64	60/64	0.92	59/64	FRSSO50060	19	4.37
0.895 / 0.906	58/64	1	0.93	60/64	FRSSO50100	19	4.62
0.907 / 0.918	58/64	1	0.94	60/64	FRSSO50100	19	4.88
0.919 / 0.930	59/64	1	0.95	61/64	FRSSO50100	23	1.13
0.931 / 0.942	60/64	1	0.96	61/64	FRSSO50100	23	1.38
0.943 / 0.955	61/64	1	0.97	62/64	FRSSO50100	23	1.64
0.956 / 0.967	61/64	1 4/64	0.98	63/64	FRSSO50104	23	1.89
0.968 / 0.979	62/64	1 4/64	0.99	63/64	FRSSO50104	23	2.15
0.980 / 0.991	63/64	1 4/64	1.00	1	FRSSO50104	23	2.40
0.992 / 1.003	1	1 4/64	1.01	1 1/64	FRSSO50104	23	2.65
1.004 / 1.015	1 1/64	1 4/64	1.02	1 1/64	FRSSO50104	23	2.91
1.016 / 1.027	1 1/64	1 8/64	1.03	1 2/64	FRSSO50108	23	3.16
1.028 / 1.039	1 2/64	1 8/64	1.04	1 3/64	FRSSO50108	23	3.42
1.040 / 1.052	1 3/64	1 8/64	1.05	1 3/64	FRSSO50108	23	3.67
1.053 / 1.064	1 4/64	1 8/64	1.06	1 4/64	FRSSO50108	23	3.92
1.065 / 1.076	1 4/64	1 8/64	1.07	1 4/64	FRSSO50108	23	4.18
1.077 / 1.088	1 5/64	1 12/64	1.08	1 5/64	FRSSO50112	23	4.43
1.089 / 1.100	1 6/64	1 12/64	1.09	1 6/64	FRSSO50112	27	0.69
1.101 / 1.112	1 7/64	1 12/64	1.10	1 6/64	FRSSO50112	27	0.94
1.113 / 1.124	1 8/64	1 12/64	1.11	1 7/64	FRSSO50112	27	1.19
1.125 / 1.136	1 8/64	1 12/64	1.12	1 8/64	FRSSO50112	27	1.45
1.137 / 1.148	1 9/64	1 16/64	1.13	1 8/64	FRSSO50116	27	1.70
1.149 / 1.161	1 10/64	1 16/64	1.14	1 9/64	FRSSO50116	27	1.96
1.162 / 1.173	1 11/64	1 16/64	1.15	1 10/64	FRSSO50116	27	2.21
1.174 / 1.185	1 11/64	1 16/64	1.16	1 10/64	FRSSO50116	27	2.46

The above Insta-Lock™ Crimp Chart is to be used ONLY for the Continental Industrial Hoses and sizes denoted "A" on pages 5-8 (Crimp Solutions by Application).
 *Using OD Measurement Method **Quality of final crimp not verified with die selections, listed closest standard die set

3/4 in. Chart A | Insta-Lock™

Insta-Lock™ 3/4 in. Crimp Chart*

Measured Hose OD, Decimal Min. / Max.	Measured Hose OD In Closest 64ths	Ferrule ID	Finished Crimp Diameter Inches	Finished Crimp Diameter Closest 64ths	Insta-Lock™ Ferrule Part #	Perma-Crimp™	
						Die Set**	Approximate Setting
1.060 / 1.071	1 4/64	1 2/16	1.11	1 7/64	FRSSO75108	27	1.19
1.072 / 1.083	1 5/64	1 2/16	1.12	1 8/64	FRSSO75108	27	1.45
1.084 / 1.095	1 6/64	1 3/16	1.13	1 8/64	FRSSO75112	27	1.70
1.096 / 1.108	1 6/64	1 3/16	1.14	1 9/64	FRSSO75112	27	1.96
1.109 / 1.120	1 7/64	1 3/16	1.15	1 10/64	FRSSO75112	27	2.21
1.121 / 1.132	1 8/64	1 3/16	1.16	1 10/64	FRSSO75112	27	2.46
1.133 / 1.144	1 9/64	1 3/16	1.17	1 11/64	FRSSO75112	27	2.72
1.145 / 1.156	1 10/64	1 4/16	1.18	1 12/64	FRSSO75116	27	2.97
1.157 / 1.168	1 10/64	1 4/16	1.19	1 12/64	FRSSO75116	27	3.23
1.169 / 1.180	1 11/64	1 4/16	1.20	1 13/64	FRSSO75116	27	3.48
1.181 / 1.192	1 12/64	1 4/16	1.21	1 13/64	FRSSO75116	27	3.73
1.193 / 1.205	1 13/64	1 4/16	1.22	1 14/64	FRSSO75116	27	3.99
1.206 / 1.217	1 13/64	1 5/16	1.23	1 15/64	FRSSO75120	27	4.24
1.218 / 1.229	1 14/64	1 5/16	1.24	1 15/64	FRSSO75120	31	0.50
1.230 / 1.241	1 15/64	1 5/16	1.25	1 16/64	FRSSO75120	31	0.75
1.242 / 1.253	1 16/64	1 5/16	1.26	1 17/64	FRSSO75120	31	1.00
1.254 / 1.265	1 17/64	1 5/16	1.27	1 17/64	FRSSO75120	31	1.26
1.266 / 1.277	1 17/64	1 6/16	1.28	1 18/64	FRSSO75124	31	1.51
1.278 / 1.289	1 18/64	1 6/16	1.29	1 19/64	FRSSO75124	31	1.77
1.290 / 1.302	1 19/64	1 6/16	1.30	1 19/64	FRSSO75124	31	2.02
1.303 / 1.314	1 20/64	1 6/16	1.31	1 20/64	FRSSO75124	31	2.27
1.315 / 1.326	1 20/64	1 6/16	1.32	1 20/64	FRSSO75124	31	2.53
1.327 / 1.338	1 21/64	1 7/16	1.33	1 21/64	FRSSO75128	31	2.78
1.339 / 1.350	1 22/64	1 7/16	1.34	1 22/64	FRSSO75128	31	3.04

The above Insta-Lock™ Crimp Chart is to be used ONLY for the Continental Industrial Hoses and sizes denoted "A" on pages 5-8 (Crimp Solutions by Application).
 *Using OD Measurement Method **Quality of final crimp not verified with die selections, listed closest standard die set

1 in. Chart A | Insta-Lock™

Insta-Lock™ 1 in. Crimp Chart*

For Ferrule Wall Thickness of .060 in.

Measured Hose OD, Decimal Min. / Max.	Measured Hose OD In Closest 64ths	Ferrule ID	Finished Crimp Diameter Inches	Finished Crimp Diameter Closest 64ths	Insta-Lock™ Ferrule Part #	Perma-Crimp™	
						Die Set**	Approximate Setting
1.300 / 1.312	1 20/64	1 28/64	1.37	1 24/64	FRSS100128	34	0.80
1.313 / 1.324	1 20/64	1 28/64	1.38	1 24/64	FRSS100128	34	1.05
1.325 / 1.336	1 21/64	1 28/64	1.39	1 25/64	FRSS100128	34	1.31
1.337 / 1.348	1 22/64	1 28/64	1.40	1 26/64	FRSS100128	34	1.56
1.349 / 1.360	1 23/64	1 28/64	1.41	1 26/64	FRSS100128	34	1.81
1.361 / 1.372	1 23/64	1 32/64	1.42	1 27/64	FRSS100132	34	2.07
1.373 / 1.384	1 24/64	1 32/64	1.43	1 28/64	FRSS100132	34	2.32
1.385 / 1.396	1 25/64	1 32/64	1.44	1 28/64	FRSS100132	34	2.58
1.397 / 1.408	1 26/64	1 32/64	1.45	1 29/64	FRSS100132	34	2.83
1.409 / 1.421	1 27/64	1 32/64	1.46	1 29/64	FRSS100132	34	3.08
1.422 / 1.433	1 27/64	1 36/64	1.47	1 30/64	FRSS100136	34	3.34
1.434 / 1.445	1 28/64	1 36/64	1.48	1 31/64	FRSS100136	34	3.59
1.446 / 1.457	1 29/64	1 36/64	1.49	1 31/64	FRSS100136	34	3.85
1.458 / 1.469	1 30/64	1 36/64	1.50	1 32/64	FRSS100136	34	4.10
1.470 / 1.481	1 30/64	1 36/64	1.51	1 33/64	FRSS100136	34	4.35
1.482 / 1.493	1 31/64	1 36/64	1.52	1 33/64	FRSS100136	34	4.61
1.494 / 1.505	1 32/64	1 40/64	1.53	1 34/64	FRSS100140	34	4.86
1.506 / 1.518	1 33/64	1 40/64	1.54	1 35/64	FRSS100140	34	5.12
1.519 / 1.530	1 34/64	1 40/64	1.55	1 35/64	FRSS100140	34	5.37
1.531 / 1.542	1 34/64	1 40/64	1.56	1 36/64	FRSS100140	34	5.62
1.543 / 1.554	1 35/64	1 40/64	1.57	1 36/64	FRSS100140	34	5.88
1.555 / 1.566	1 36/64	1 44/64	1.58	1 37/64	FRSS100144	34	6.13
1.567 / 1.578	1 37/64	1 44/64	1.59	1 38/64	FRSS100144	34	6.39
1.579 / 1.590	1 37/64	1 44/64	1.60	1 38/64	FRSS100144	34	6.64
1.591 / 1.602	1 38/64	1 44/64	1.61	1 39/64	FRSS100144	34	6.39
1.603 / 1.615	1 39/64	1 44/64	1.62	1 40/64	FRSS100144	34	7.15

The above Insta-Lock™ Crimp Chart is to be used ONLY for the Continental Industrial Hoses and sizes denoted on pages 5-8 (Crimp Solutions by Application) and is for ferrule wall thickness of .060".

*Using OD Measurement Method **Quality of final crimp not verified with die selections, listed closest standard die set

1¼ in. Chart A | Insta-Lock™

Insta-Lock™ 1¼ in. Crimp Chart*

Perma-Crimp™

Measured Hose OD, Decimal Min. / Max.	Measured Hose OD In Closest 64ths	Ferrule ID	Finished Crimp Diameter Inches	Finished Crimp Diameter Closest 64ths	Stainless Steel Insta-Lock™ Ferrule Part #	Perma-Crimp™	
						Die Set**	Approximate Setting
1.548 / 1.559	1 35/64	1 44/64	1.63	1 40/64	FSSR125144	41	0.40
1.560 / 1.571	1 36/64	1 44/64	1.64	1 41/64	FSSR125144	41	0.66
1.572 / 1.583	1 37/64	1 44/64	1.65	1 42/64	FSSR125144	41	0.91
1.584 / 1.595	1 38/64	1 44/64	1.66	1 42/64	FSSR125144	41	1.16
1.596 / 1.608	1 38/64	1 44/64	1.67	1 43/64	FSSR125144	41	1.42
1.609 / 1.620	1 39/64	1 48/64	1.68	1 44/64	FSSR125148	41	1.67
1.621 / 1.632	1 40/64	1 48/64	1.69	1 44/64	FSSR125148	41	1.93
1.633 / 1.644	1 41/64	1 48/64	1.70	1 45/64	FSSR125148	41	2.18
1.645 / 1.656	1 42/64	1 48/64	1.71	1 45/64	FSSR125148	41	2.43
1.657 / 1.668	1 42/64	1 48/64	1.72	1 46/64	FSSR125148	41	2.69
1.669 / 1.680	1 43/64	1 52/64	1.73	1 47/64	FSSR125152	41	2.94
1.681 / 1.692	1 44/64	1 52/64	1.74	1 47/64	FSSR125152	41	3.20
1.693 / 1.705	1 45/64	1 52/64	1.75	1 48/64	FSSR125152	41	3.45
1.706 / 1.717	1 45/64	1 52/64	1.76	1 49/64	FSSR125152	41	3.70
1.718 / 1.729	1 46/64	1 52/64	1.77	1 49/64	FSSR125152	41	3.96
1.730 / 1.741	1 47/64	1 56/64	1.78	1 50/64	FSSR125156	41	4.21
1.742 / 1.753	1 48/64	1 56/64	1.79	1 51/64	FSSR125156	45	0.47
1.754 / 1.765	1 49/64	1 56/64	1.80	1 51/64	FSSR125156	45	0.72
1.766 / 1.777	1 49/64	1 56/64	1.81	1 52/64	FSSR125156	45	0.97
1.778 / 1.789	1 50/64	1 56/64	1.82	1 52/64	FSSR125156	45	1.23
1.790 / 1.802	1 51/64	1 60/64	1.83	1 53/64	FSSR125160	45	1.48
1.803 / 1.814	1 52/64	1 60/64	1.84	1 54/64	FSSR125160	45	1.74
1.815 / 1.826	1 52/64	1 60/64	1.85	1 54/64	FSSR125160	45	1.99
1.827 / 1.838	1 53/64	1 60/64	1.86	1 55/64	FSSR125160	45	2.24
1.839 / 1.850	1 54/64	1 60/64	1.87	1 56/64	FSSR125160	45	2.50
1.851 / 1.862	1 55/64	1 60/64	1.88	1 56/64	FSSR125160	45	2.75

The above Insta-Lock™ Crimp Chart is to be used ONLY for the Continental Industrial Hoses and sizes denoted "A" on pages 5-8 (Crimp Solutions by Application). *Using OD Measurement Method **Quality of final crimp not verified with die selections, listed closest standard die set

1½ in. Chart A | Insta-Lock™

Insta-Lock™ 1½ in. Crimp Chart*

Measured Hose OD, Decimal Min. / Max.	Measured Hose OD In Closest 64ths		Finished Crimp Diameter Inches	Finished Crimp Diameter Closest 64ths	Stainless Steel Insta-Lock™ Ferrule Part #	Perma-Crimp™	
	Ferrule ID					Die Set**	Approximate Setting
1.798 / 1.809	1 51/64	1 60/64	1.88	1 56/64	FRSS150160	45	2.75
1.810 / 1.821	1 52/64	1 60/64	1.89	1 57/64	FRSS150160	45	3.01
1.822 / 1.833	1 53/64	1 60/64	1.90	1 58/64	FRSS150160	45	3.26
1.834 / 1.845	1 54/64	1 60/64	1.91	1 58/64	FRSS150160	45	3.51
1.846 / 1.858	1 54/64	1 60/64	1.92	1 59/64	FRSS150160	45	3.77
1.859 / 1.870	1 55/64	2	1.93	1 60/64	FRSS150200	45	4.02
1.871 / 1.882	1 56/64	2	1.94	1 60/64	FRSS150200	45	4.28
1.883 / 1.894	1 57/64	2	1.95	1 61/64	FRSS150200	45	4.53
1.895 / 1.906	1 58/64	2	1.96	1 61/64	FRSS150200	45	4.78
1.907 / 1.918	1 58/64	2	1.97	1 62/64	FRSS150200	45	5.04
1.919 / 1.930	1 59/64	2 4/64	1.98	1 63/64	FRSS150204	45	5.29
1.931 / 1.942	1 60/64	2 4/64	1.99	1 63/64	FRSS150204	50	0.55
1.943 / 1.955	1 61/64	2 4/64	2.00	2	FRSS150204	50	0.80
1.956 / 1.967	1 61/64	2 4/64	2.01	2 1/64	FRSS150204	50	1.05
1.968 / 1.979	1 62/64	2 4/64	2.02	2 1/64	FRSS150204	50	1.31
1.980 / 1.991	1 63/64	2 8/64	2.03	2 2/64	FRSS150208	50	1.56
1.992 / 2.003	2	2 8/64	2.04	2 3/64	FRSS150208	50	1.82
2.004 / 2.015	2 1/64	2 8/64	2.05	2 3/64	FRSS150208	50	2.07
2.016 / 2.027	2 1/64	2 8/64	2.06	2 4/64	FRSS150208	50	2.32
2.028 / 2.039	2 2/64	2 8/64	2.07	2 4/64	FRSS150208	50	2.58
2.040 / 2.052	2 3/64	2 12/64	2.08	2 5/64	FRSS150212	50	2.83
2.053 / 2.064	2 4/64	2 12/64	2.09	2 6/64	FRSS150212	50	3.09
2.065 / 2.076	2 4/64	2 12/64	2.10	2 6/64	FRSS150212	50	3.34
2.077 / 2.088	2 5/64	2 12/64	2.11	2 7/64	FRSS150212	50	3.59
2.089 / 2.100	2 6/64	2 12/64	2.12	2 8/64	FRSS150212	50	3.85
2.101 / 2.112	2 7/64	2 12/64	2.13	2 8/64	FRSS150212	50	4.10
2.113 / 2.124	2 8/64	2 16/64	2.14	2 9/64	FRSS150216	50	4.36
2.125 / 2.136	2 8/64	2 16/64	2.15	2 10/64	FRSS150216	50	4.61
2.137 / 2.148	2 9/64	2 16/64	2.16	2 10/64	FRSS150216	50	4.86
2.149 / 2.161	2 10/64	2 16/64	2.17	2 11/64	FRSS150216	50	5.12
2.162 / 2.173	2 11/64	2 16/64	2.18	2 12/64	FRSS150216	50	5.37

The above Insta-Lock™ Crimp Chart is to be used ONLY for the Continental Industrial Hoses and sizes denoted "A" on pages 5-8 (Crimp Solutions by Application).
 *Using OD Measurement Method **Quality of final crimp not verified with die selections, listed closest standard die set

2 in. Chart A | Insta-Lock™

Insta-Lock™ 2 in. Crimp Chart*

Measured Hose OD, Decimal Min. / Max.	Measured Hose OD In Closest 64ths		Finished Crimp Diameter Inches	Finished Crimp Diameter Closest 64ths	Stainless Steel Insta-Lock™ Ferrule Part #	Perma-Crimp™	
	Ferrule ID					Die Set**	Approximate Setting
2.346 / 2.358	2 22/64	2 32/64	2.42	2 27/64	FRSS200232	56	5.47
2.359 / 2.370	2 23/64	2 32/64	2.43	2 28/64	FRSS200232	56	5.72
2.371 / 2.382	2 24/64	2 32/64	2.44	2 28/64	FRSS200232	56	5.98
2.383 / 2.394	2 25/64	2 32/64	2.45	2 29/64	FRSS200232	56	6.23
2.395 / 2.406	2 26/64	2 32/64	2.46	2 29/64	FRSS200232	56	6.48
2.407 / 2.418	2 26/64	2 32/64	2.47	2 30/64	FRSS200232	62	0.74
2.419 / 2.430	2 27/64	2 36/64	2.48	2 31/64	FRSS200236	62	0.99
2.431 / 2.442	2 28/64	2 36/64	2.49	2 31/64	FRSS200236	62	1.25
2.443 / 2.455	2 29/64	2 36/64	2.50	2 32/64	FRSS200236	62	1.50
2.456 / 2.467	2 29/64	2 36/64	2.51	2 33/64	FRSS200236	62	1.75
2.468 / 2.479	2 30/64	2 36/64	2.52	2 33/64	FRSS200236	62	2.01
2.480 / 2.491	2 31/64	2 40/64	2.53	2 34/64	FRSS200240	62	2.26
2.492 / 2.503	2 32/64	2 40/64	2.54	2 35/64	FRSS200240	62	2.52
2.504 / 2.515	2 33/64	2 40/64	2.55	2 35/64	FRSS200240	62	2.77
2.516 / 2.527	2 33/64	2 40/64	2.56	2 36/64	FRSS200240	62	3.02
2.528 / 2.539	2 34/64	2 40/64	2.57	2 36/64	FRSS200240	62	3.28
2.540 / 2.552	2 35/64	2 44/64	2.58	2 37/64	FRSS200244	62	3.53
2.553 / 2.564	2 36/64	2 44/64	2.59	2 38/64	FRSS200244	62	3.79
2.565 / 2.576	2 36/64	2 44/64	2.60	2 38/64	FRSS200244	62	4.04
2.577 / 2.588	2 37/64	2 44/64	2.61	2 39/64	FRSS200244	62	4.29
2.589 / 2.600	2 38/64	2 44/64	2.62	2 40/64	FRSS200244	62	4.55
2.601 / 2.612	2 39/64	2 48/64	2.63	2 40/64	FRSS200248	62	4.80
2.613 / 2.624	2 40/64	2 48/64	2.64	2 41/64	FRSS200248	62	5.06
2.625 / 2.636	2 40/64	2 48/64	2.65	2 42/64	FRSS200248	62	5.31
2.637 / 2.648	2 41/64	2 48/64	2.66	2 42/64	FRSS200248	62	5.56
2.649 / 2.661	2 42/64	2 48/64	2.67	2 43/64	FRSS200248	62	5.82
2.662 / 2.673	2 43/64	2 52/64	2.68	2 44/64	FRSS200252	62	6.07
2.674 / 2.685	2 43/64	2 52/64	2.69	2 44/64	FRSS200252	62	6.33
2.686 / 2.697	2 44/64	2 52/64	2.70	2 45/64	FRSS200252	62	6.58
2.698 / 2.709	2 45/64	2 52/64	2.71	2 45/64	FRSS200252	62	6.83
2.710 / 2.721	2 46/64	2 52/64	2.72	2 46/64	FRSS200252	62	7.09
2.722 / 2.733	2 47/64	2 56/64	2.73	2 47/64	FRSS200256	62	7.34
2.734 / 2.745	2 47/64	2 56/64	2.74	2 47/64	FRSS200256	62	7.60
2.746 / 2.758	2 48/64	2 56/64	2.75	2 48/64	FRSS200256	62	7.85
2.759 / 2.770	2 49/64	2 56/64	2.76	2 49/64	FRSS200256	69	1.10

The above Insta-Lock™ Crimp Chart is to be used ONLY for the Continental Industrial Hoses and sizes denoted "A" on pages 5-8 (Crimp Solutions by Application).
 *Using OD Measurement Method **Quality of final crimp not verified with die selections, listed closest standard die set

2½ in. Chart A | Insta-Lock™

Insta-Lock™ 2½ in. Crimp Chart*

Measured Hose OD, Decimal Min. / Max.	Measured Hose OD In Closest 64ths	Ferrule ID	Finished Crimp Diameter Inches	Finished Crimp Diameter Closest 64ths	Stainless Steel Insta-Lock™ Ferrule Part #	Perma-Crimp™	
						Die Set**	Approximate Setting
2.834 / 2.845	2 54/64	3	2.91	2 58/64	FRSS250300	69	4.91
2.846 / 2.858	2 54/64	3	2.92	2 59/64	FRSS250300	69	5.17
2.859 / 2.870	2 55/64	3	2.93	2 60/64	FRSS250300	69	5.42
2.871 / 2.882	2 56/64	3	2.94	2 60/64	FRSS250300	69	5.68
2.883 / 2.894	2 57/64	3	2.95	2 61/64	FRSS250300	69	5.93
2.895 / 2.906	2 58/64	3 4/64	2.96	2 61/64	FRSS250304	74	1.18
2.907 / 2.918	2 58/64	3 4/64	2.97	2 62/64	FRSS250304	74	1.44
2.919 / 2.930	2 59/64	3 4/64	2.98	2 63/64	FRSS250304	74	1.69
2.931 / 2.942	2 60/64	3 4/64	2.99	2 63/64	FRSS250304	74	1.95
2.943 / 2.955	2 61/64	3 4/64	3.00	3	FRSS250304	74	2.20
2.956 / 2.967	2 61/64	3 8/64	3.01	3 1/64	FRSS250308	74	2.45
2.968 / 2.979	2 62/64	3 8/64	3.02	3 1/64	FRSS250308	74	2.71
2.980 / 2.991	2 63/64	3 8/64	3.03	3 2/64	FRSS250308	74	2.96
2.992 / 3.003	3	3 8/64	3.04	3 3/64	FRSS250308	74	3.22
3.004 / 3.015	3 1/64	3 8/64	3.05	3 3/64	FRSS250308	74	3.47
3.016 / 3.027	3 1/64	3 12/64	3.06	3 4/64	FRSS250312	74	3.72
3.028 / 3.039	3 2/64	3 12/64	3.07	3 4/64	FRSS250312	74	3.98
3.040 / 3.052	3 3/64	3 12/64	3.08	3 5/64	FRSS250312	74	4.23
3.053 / 3.064	3 4/64	3 12/64	3.09	3 6/64	FRSS250312	74	4.49
3.065 / 3.076	3 4/64	3 12/64	3.10	3 6/64	FRSS250312	74	4.74
3.077 / 3.088	3 5/64	3 16/64	3.11	3 7/64	FRSS250316	74	4.99
3.089 / 3.100	3 6/64	3 16/64	3.12	3 8/64	FRSS250316	78	1.25
3.101 / 3.112	3 7/64	3 16/64	3.13	3 8/64	FRSS250316	78	1.50
3.113 / 3.124	3 8/64	3 16/64	3.14	3 9/64	FRSS250316	78	1.76
3.125 / 3.136	3 8/64	3 16/64	3.15	3 10/64	FRSS250316	78	2.01
3.137 / 3.148	3 9/64	3 20/64	3.16	3 10/64	FRSS250320	78	2.26
3.149 / 3.161	3 10/64	3 20/64	3.17	3 11/64	FRSS250320	78	2.52
3.162 / 3.173	3 11/64	3 20/64	3.18	3 12/64	FRSS250320	78	2.77
3.174 / 3.185	3 11/64	3 20/64	3.19	3 12/64	FRSS250320	78	3.03
3.186 / 3.197	3 12/64	3 20/64	3.20	3 13/64	FRSS250320	78	3.28

The above Insta-Lock™ Crimp Chart is to be used ONLY for the Continental Industrial Hoses and sizes denoted "A" on pages 5-8 (Crimp Solutions by Application).
 *Using OD Measurement Method **Quality of final crimp not verified with die selections, listed closest standard die set

3 in. Chart A | Insta-Lock™

Insta-Lock™ 3 in. Crimp Chart*

For Ferrule Wall Thickness of .080 in.

Measured Hose OD, Decimal Min. / Max.	Measured Hose OD In Closest 64ths	Ferrule ID	Finished Crimp Diameter Inches	Finished Crimp Diameter Closest 64ths	Stainless Steel Insta-Lock™ Ferrule Part #	Perma-Crimp™	
						Die Set**	Approximate Setting
3.359 / 3.370	3 23/64	3 32/64	3.46	3 29/64	FRSS300332	86	1.88
3.371 / 3.382	3 24/64	3 32/64	3.47	3 30/64	FRSS300332	86	2.14
3.383 / 3.394	3 25/64	3 32/64	3.48	3 31/64	FRSS300332	86	2.39
3.395 / 3.406	3 26/64	3 36/64	3.49	3 31/64	FRSS300336	86	2.65
3.407 / 3.418	3 26/64	3 36/64	3.50	3 32/64	FRSS300336	86	2.90
3.419 / 3.430	3 27/64	3 36/64	3.51	3 33/64	FRSS300336	86	3.15
3.431 / 3.442	3 28/64	3 36/64	3.52	3 33/64	FRSS300336	86	3.41
3.443 / 3.455	3 29/64	3 36/64	3.53	3 34/64	FRSS300336	86	3.66
3.456 / 3.467	3 29/64	3 40/64	3.54	3 35/64	FRSS300340	86	3.92
3.468 / 3.479	3 30/64	3 40/64	3.55	3 35/64	FRSS300340	86	4.17
3.480 / 3.491	3 31/64	3 40/64	3.56	3 36/64	FRSS300340	90	0.42
3.492 / 3.503	3 32/64	3 40/64	3.57	3 36/64	FRSS300340	90	0.93
3.516 / 3.527	3 33/64	3 44/64	3.59	3 38/64	FRSS300344	90	1.19
3.528 / 3.539	3 34/64	3 44/64	3.60	3 38/64	FRSS300344	90	1.44
3.540 / 3.552	3 35/64	3 44/64	3.61	3 39/64	FRSS300344	90	1.69
3.553 / 3.564	3 36/64	3 44/64	3.62	3 40/64	FRSS300344	90	1.95
3.565 / 3.576	3 36/64	3 44/64	3.63	3 40/64	FRSS300344	90	2.20
3.577 / 3.588	3 37/64	3 48/64	3.64	3 41/64	FRSS300348	90	2.46
3.589 / 3.600	3 38/64	3 48/64	3.65	3 42/64	FRSS300348	90	2.71
3.601 / 3.612	3 39/64	3 48/64	3.66	3 42/64	FRSS300348	90	2.96
3.613 / 3.624	3 40/64	3 48/64	3.67	3 43/64	FRSS300348	90	3.22
3.625 / 3.636	3 40/64	3 48/64	3.68	3 44/64	FRSS300348	90	3.47
3.637 / 3.648	3 41/64	3 52/64	3.69	3 44/64	FRSS300352	90	3.73
3.649 / 3.661	3 42/64	3 52/64	3.70	3 45/64	FRSS300352	90	3.98
3.662 / 3.673	3 43/64	3 52/64	3.71	3 45/64	FRSS300352	90	4.23
3.674 / 3.685	3 43/64	3 52/64	3.72	3 46/64	FRSS300352	90	4.49
3.686 / 3.697	3 44/64	3 52/64	3.73	3 47/64	FRSS300352	90	4.74
3.698 / 3.709	3 45/64	3 56/64	3.74	3 47/64	FRSS300356	90	5.00
3.710 / 3.721	3 46/64	3 56/64	3.75	3 48/64	FRSS300356	90	5.25
3.722 / 3.733	3 47/64	3 56/64	3.76	3 49/64	FRSS300356	90	5.50
3.734 / 3.745	3 47/64	3 56/64	3.77	3 49/64	FRSS300356	90	5.76
3.746 / 3.758	3 48/64	3 56/64	3.78	3 50/64	FRSS300356	90	6.01
3.759 / 3.770	3 49/64	3 56/64	3.79	3 51/64	FRSS300356	90	6.27
3.771 / 3.782	3 50/64	3 60/64	3.80	3 51/64	FRSS300360	90	6.52
3.783 / 3.794	3 50/64	3 15/16	3.81	3 52/64	FRSS300315	90	6.77

The above Insta-Lock™ Crimp Chart is to be used ONLY for the Continental Industrial Hoses and sizes denoted "A" on pages 5-8 (Crimp Solutions by Application) and is for ferrule wall thickness of .080".

*Using OD Measurement Method **Quality of final crimp not verified with die selections, listed closest standard die set

4 in. Chart A | Insta-Lock™

Insta-Lock™ 4 in. Crimp Chart*

Measured Hose OD, Decimal Min. / Max.	Measured Hose OD In Closest 64ths		Finished Crimp Diameter Inches	Finished Crimp Diameter Closest 64ths	Stainless Steel Insta-Lock™ Ferrule Part #	Perma-Crimp™	
	Ferrule ID					Die Set**	Approximate Setting
4.448 / 4.459	4 29/64	4 40/64	4.54	4 35/64	FRSS400440	114	1.32
4.460 / 4.472	4 30/64	4 40/64	4.55	4 35/64	FRSS400440	114	1.57
4.473 / 4.484	4 31/64	4 40/64	4.56	4 36/64	FRSS400440	114	1.82
4.485 / 4.496	4 31/64	4 40/64	4.57	4 36/64	FRSS400440	114	2.08
4.497 / 4.508	4 32/64	4 40/64	4.58	4 37/64	FRSS400440	114	2.33
4.509 / 4.520	4 33/64	4 44/64	4.59	4 38/64	FRSS400444	114	2.59
4.521 / 4.532	4 34/64	4 44/64	4.60	4 38/64	FRSS400444	114	2.84
4.533 / 4.544	4 34/64	4 44/64	4.61	4 39/64	FRSS400444	114	3.09
4.545 / 4.556	4 35/64	4 44/64	4.62	4 40/64	FRSS400444	114	3.35
4.557 / 4.568	4 36/64	4 44/64	4.63	4 40/64	FRSS400444	114	3.60
4.569 / 4.581	4 37/64	4 48/64	4.64	4 41/64	FRSS400448	114	3.86
4.582 / 4.593	4 38/64	4 48/64	4.65	4 42/64	FRSS400448	114	4.11
4.594 / 4.605	4 38/64	4 48/64	4.66	4 42/64	FRSS400448	114	4.36
4.606 / 4.617	4 39/64	4 48/64	4.67	4 43/64	FRSS400448	114	4.62
4.618 / 4.629	4 40/64	4 48/64	4.68	4 44/64	FRSS400448	114	4.87
4.630 / 4.641	4 41/64	4 52/64	4.69	4 44/64	FRSS400452	118	1.13
4.642 / 4.653	4 41/64	4 52/64	4.70	4 45/64	FRSS400452	118	1.38
4.654 / 4.665	4 42/64	4 52/64	4.71	4 45/64	FRSS400452	118	1.63
4.666 / 4.678	4 43/64	4 52/64	4.72	4 46/64	FRSS400452	118	1.89
4.679 / 4.690	4 44/64	4 52/64	4.73	4 47/64	FRSS400452	118	2.14
4.691 / 4.702	4 45/64	4 52/64	4.74	4 47/64	FRSS400452	118	2.40
4.703 / 4.714	4 45/64	4 56/64	4.75	4 48/64	FRSS400456	118	2.65
4.715 / 4.726	4 46/64	4 56/64	4.76	4 49/64	FRSS400456	118	2.90
4.727 / 4.738	4 47/64	4 56/64	4.77	4 49/64	FRSS400456	118	3.16
4.739 / 4.750	4 48/64	4 56/64	4.78	4 50/64	FRSS400456	118	3.41
4.751 / 4.762	4 48/64	4 56/64	4.79	4 51/64	FRSS400456	118	3.67
4.763 / 4.775	4 49/64	4 60/64	4.80	4 51/64	FRSS400460	118	3.92
4.776 / 4.787	4 50/64	4 60/64	4.81	4 52/64	FRSS400460	118	4.17
4.788 / 4.799	4 51/64	4 60/64	4.82	4 52/64	FRSS400460	118	4.43
4.800 / 4.811	4 52/64	4 60/64	4.83	4 53/64	FRSS400460	118	4.68
4.812 / 4.823	4 52/64	4 60/64	4.84	4 54/64	FRSS400460	118	4.94
4.824 / 4.835	4 53/64	5	4.85	4 54/64	FRSS400500	118	5.19
4.836 / 4.847	4 54/64	5	4.86	4 55/64	FRSS400500	118	5.44
4.848 / 4.859	4 55/64	5	4.87	4 56/64	FRSS400500	118	5.70
4.860 / 4.872	4 55/64	5	4.88	4 56/64	FRSS400500	118	5.95
4.873 / 4.884	4 56/64	5	4.89	4 57/64	FRSS400500	118	6.21

The above Insta-Lock™ Crimp Chart is to be used ONLY for the Continental Industrial Hoses and sizes denoted "A" on pages 5-8 (Crimp Solutions by Application). *Using OD Measurement Method **Quality of final crimp not verified with die selections, listed closest standard die set



5 in. Chart A | Insta-Lock™

Insta-Lock™ 5 in. Crimp Chart*

Measured Hose OD, Decimal Min. / Max.	Measured Hose OD In Closest 64ths		Finished Crimp Diameter Inches	Finished Crimp Diameter Closest 64ths	Stainless Steel Insta-Lock™ Ferrule Part #	Perma-Crimp™	
	Ferrule ID					Die Set**	Approximate Setting
5.586 / 5.601	5 38/64	5 52/64	5.710	5 45/64	FRSS500552		
5.602 / 5.617	5 39/64	5 52/64	5.722	5 46/64	FRSS500552		
5.618 / 5.632	5 40/64	5 52/64	5.734	5 47/64	FRSS500552		
5.633 / 5.648	5 41/64	5 52/64	5.747	5 48/64	FRSS500552		
5.649 / 5.663	5 42/64	5 52/64	5.759	5 49/64	FRSS500552		
5.664 / 5.679	5 43/64	5 52/64	5.771	5 49/64	FRSS500552		
5.68 / 5.695	5 44/64	5 52/64	5.784	5 50/64	FRSS500552		
5.696 / 5.71	5 45/64	5 52/64	5.796	5 51/64	FRSS500552		
5.711 / 5.726	5 46/64	5 52/64	5.809	5 52/64	FRSS500552		
5.727 / 5.742	5 47/64	5 52/64	5.821	5 53/64	FRSS500552		
5.743 / 5.757	5 48/64	5 52/64	5.833	5 53/64	FRSS500552		
5.758 / 5.773	5 49/64	5 52/64	5.846	5 54/64	FRSS500552		
5.774 / 5.788	5 50/64	5 60/64	5.858	5 55/64	FRSS500600		
5.789 / 5.804	5 51/64	5 60/64	5.870	5 56/64	FRSS500600		
5.805 / 5.82	5 52/64	5 60/64	5.883	5 56/64	FRSS500600		
5.821 / 5.835	5 53/64	5 60/64	5.895	5 57/64	FRSS500600		
5.836 / 5.851	5 54/64	5 60/64	5.907	5 58/64	FRSS500600		
5.852 / 5.867	5 55/64	5 60/64	5.920	5 59/64	FRSS500600		
5.868 / 5.882	5 56/64	5 60/64	5.932	5 60/64	FRSS500600		
5.883 / 5.898	5 57/64	5 60/64	5.944	5 60/64	FRSS500600		
5.899 / 5.913	5 58/64	5 60/64	5.957	5 61/64	FRSS500600		
5.914 / 5.929	5 59/64	5 60/64	5.969	5 62/64	FRSS500600		
5.93 / 5.945	5 60/64	5 60/64	5.981	5 63/64	FRSS500600		
5.946 / 5.96	5 61/64	6 8/64	5.994	6	FRSS500608		
5.961 / 5.976	5 62/64	6 8/64	6.006	6	FRSS500608		
5.977 / 5.992	5 63/64	6 8/64	6.018	6 1/64	FRSS500608		
5.993 / 6.007	6	6 8/64	6.031	6 2/64	FRSS500608		
6.008 / 6.023	6 1/64	6 8/64	6.043	6 3/64	FRSS500608		
6.024 / 6.038	6 2/64	6 8/64	6.055	6 4/64	FRSS500608		
6.039 / 6.054	6 3/64	6 8/64	6.068	6 4/64	FRSS500608		
6.055 / 6.07	6 4/64	6 8/64	6.080	6 5/64	FRSS500608		

The above Insta-Lock™ Crimp Chart is to be used ONLY for the Continental Industrial Hoses and sizes denoted "A" on pages 5-8 (Crimp Solutions by Application). *Using OD Measurement Method **Quality of final crimp not verified with die selections, listed closest standard die set



6 in. Chart A | Insta-Lock™

Insta-Lock™ 6 in. Crimp Chart*

Measured Hose OD, Decimal Min. / Max.	Measured Hose OD In Closest 64ths	Finished Crimp Diameter Inches	Finished Crimp Diameter Closest 64ths	Stainless Steel Insta-Lock™ Ferrule Part #	Perma-Crimp™		
					Die Set**	Approximate Setting	
6.507 / 6.521	6 34/64	6 56/64	6.68	6 43/64	FRSS600656	166	3.63
6.539 / 6.553	6 35/64	6 56/64	6.69	6 44/64	FRSS600656	166	3.96
6.555 / 6.569	6 36/64	6 56/64	6.70	6 45/64	FRSS600656	166	4.28
6.571 / 6.585	6 37/64	6 56/64	6.72	6 46/64	FRSS600656	166	4.61
6.585 / 6.599	6 38/64	6 56/64	6.73	6 47/64	FRSS600656	166	4.94
6.601 / 6.615	6 39/64	6 56/64	6.74	6 48/64	FRSS600656	166	5.27
6.617 / 6.631	6 40/64	6 56/64	6.76	6 48/64	FRSS600656	166	5.59
6.633 / 6.647	6 41/64	6 56/64	6.77	6 49/64	FRSS600656	166	5.92
6.649 / 6.663	6 42/64	6 56/64	6.78	6 50/64	FRSS600656	166	6.25
6.663 / 6.677	6 43/64	6 56/64	6.79	6 51/64	FRSS600656	166	6.58
6.679 / 6.693	6 44/64	6 56/64	6.81	6 52/64	FRSS600656	166	6.90
6.695 / 6.709	6 45/64	6 56/64	6.82	6 52/64	FRSS600656	166	7.23
6.711 / 6.725	6 46/64	6 56/64	6.83	6 53/64	FRSS600656	166	7.56
6.727 / 6.741	6 47/64	6 56/64	6.85	6 54/64	FRSS600656	166	7.88
6.743 / 6.757	6 48/64	6 56/64	6.86	6 55/64	FRSS600656	166	8.21
6.757 / 6.771	6 49/64	6 56/64	6.87	6 56/64	FRSS600656	166	8.54
6.773 / 6.787	6 50/64	7 8/64	6.88	6 57/64	FRSS600708	166	8.87
6.789 / 6.803	6 51/64	7 8/64	6.90	6 57/64	FRSS600708	166	9.19
6.805 / 6.819	6 52/64	7 8/64	6.91	6 58/64	FRSS600708	166	9.52
6.821 / 6.835	6 53/64	7 8/64	6.92	6 59/64	FRSS600708	166	9.85
6.835 / 6.849	6 54/64	7 8/64	6.94	6 60/64	FRSS600708		
6.851 / 6.865	6 55/64	7 8/64	6.95	6 61/64	FRSS600708		
6.867 / 6.881	6 56/64	7 8/64	6.96	6 62/64	FRSS600708		
6.883 / 6.897	6 57/64	7 8/64	6.97	6 62/64	FRSS600708		
6.899 / 6.913	6 58/64	7 8/64	6.99	6 63/64	FRSS600708		
6.913 / 6.927	6 59/64	7 8/64	7.00	7	FRSS600708		
6.929 / 6.943	6 60/64	7 8/64	7.01	7 1/64	FRSS600708		
6.945 / 6.959	6 61/64	7 8/64	7.03	7 2/64	FRSS600708	178	0.47
6.961 / 6.975	6 62/64	7 8/64	7.04	7 3/64	FRSS600708	178	0.80
6.977 / 6.991	6 63/64	7 8/64	7.05	7 3/64	FRSS600708	178	1.12
6.993 / 7.007	7	7 8/64	7.07	7 4/64	FRSS600708	178	1.45
7.007 / 7.021	7 1/64	7 8/64	7.08	7 5/64	FRSS600708	178	1.78
7.023 / 7.037	7 2/64	7 24/64	7.09	7 6/64	FRSS600724	178	2.11
7.039 / 7.053	7 3/64	7 24/64	7.10	7 7/64	FRSS600724	178	2.43
6.528 / 6.535	7 4/64	7 24/64	7.12	7 7/64	FRSS600724	178	2.76
6.536 / 6.543	7 5/64	7 24/64	7.13	7 8/64	FRSS600724	178	3.09
6.543 / 6.550	7 6/64	7 24/64	7.14	7 9/64	FRSS600724	178	3.42
6.551 / 6.558	7 7/64	7 24/64	7.16	7 10/64	FRSS600724	178	3.74
6.559 / 6.566	7 8/64	7 24/64	7.17	7 11/64	FRSS600724	178	4.07
6.567 / 6.574	7 9/64	7 24/64	7.18	7 12/64	FRSS600724	178	4.40
6.575 / 6.582	7 10/64	7 24/64	7.19	7 12/64	FRSS600724	178	4.73
6.582 / 6.589	7 11/64	7 24/64	7.21	7 13/64	FRSS600724	178	5.05

The above Insta-Lock™ Crimp Chart is to be used ONLY for the Continental Industrial Hoses and sizes denoted "A" on pages 5-8 (Crimp Solutions by Application).

*Using OD Measurement Method **Quality of final crimp not verified with die selections, listed closest standard die set

2 in. Chart B | Infinity™/Paladin®/Insta-Lock™

Insta-Lock™ 2 in. Crimp Chart*

For Infinity™/Paladin® Crimp Sleeves on Infinity™/Paladin® Hose									Perma-Crimp™	
Hose OD	Hose OD 64ths	Wall	Crimp Diameter	Crimp Diameter 64ths	Ferrule ID	Ferrule Part #	Sleeve ID	Sleeve Part #	Die Set**	Setting
2.64	2 41/64	0.32	2.68	2 44/64	2 48/64	FRSS200248	3	CSSS200300	62	6.09
2.66	2 42/64	0.33	2.69	2 44/64	2 52/64	FRSS200252	3	CSSS200300	62	6.43
2.68	2 44/64	0.34	2.71	2 45/64	2 52/64	FRSS200252	3	CSSS200300	62	6.76
2.70	2 45/64	0.35	2.72	2 46/64	2 52/64	FRSS200252	3	CSSS200300	69	0.09
2.72	2 46/64	0.36	2.73	2 47/64	2 56/64	FRSS200256	3	CSSS200300	69	0.42
2.74	2 47/64	0.37	2.75	2 48/64	2 56/64	FRSS200256	3	CSSS200300	69	0.75
2.76	2 49/64	0.38	2.76	2 49/64	2 56/64	FRSS200256	3	CSSS200300	69	1.08
2.78	2 50/64	0.39	2.77	2 49/64	2 60/64	FRSS200260	3	CSSS200300	69	1.41
2.80	2 51/64	0.40	2.78	2 50/64	2 60/64	FRSS200260	3	CSSS200300	69	1.74
2.82	2 52/64	0.41	2.80	2 51/64	2 60/64	FRSS200260	3	CSSS200300	69	2.07
2.84	2 54/64	0.42	2.81	2 52/64	–	–	3	CSSS200300	69	2.40
2.86	2 55/64	0.43	2.82	2 53/64	–	–	3	CSSS200300	69	2.73
2.88	2 56/64	0.44	2.84	2 53/64	–	–	3	CSSS200300	69	3.06
2.90	2 58/64	0.45	2.85	2 54/64	–	–	3	CSSS200300	69	3.39
2.92	2 59/64	0.46	2.86	2 55/64	–	–	3	CSSS200300	69	3.72
2.94	2 60/64	0.47	2.88	2 56/64	–	–	3	CSSS200300	69	4.05

Current Paladin® Crimp Sleeve CSSS200302 has been replaced by CSSS200300.

Over 75 psi it is recommended using Insta-Lock™ in combination with banding coil.

*Using OD Measurement Method **Quality of final crimp not verified with die selections, listed closest standard die set

3 in. Chart B | Infinity™/Paladin®/Insta-Lock™

Insta-Lock™ 3 in. Crimp Chart*

For Infinity™/Paladin® Crimp Sleeves on Infinity™/Paladin® Hose

									Perma-Crimp™	
Hose OD	Hose OD 64ths	Wall	Crimp Diameter	Crimp Diameter 64ths	Ferrule ID	Ferrule Part #	Sleeve ID	Sleeve Part #	Die Set**	Setting
3.64	3 41/64	0.32	3.73	3 47/64	3 52/64	FRSS300352	4	CSSS300400	90	4.76
3.66	3 42/64	0.33	3.74	3 48/64	3 52/64	FRSS300352	4	CSSS300400	90	5.10
3.68	3 44/64	0.34	3.76	3 48/64	3 52/64	FRSS300352	4	CSSS300400	90	5.43
3.70	3 45/64	0.35	3.77	3 49/64	3 56/64	FRSS300356	4	CSSS300400	90	5.76
3.72	3 46/64	0.36	3.78	3 50/64	3 56/64	FRSS300356	4	CSSS300400	90	6.09
3.74	3 47/64	0.37	3.80	3 51/64	3 56/64	FRSS300356	4	CSSS300400	90	6.42
3.76	3 49/64	0.38	3.81	3 52/64	3 60/64	FRSS300360	4	CSSS300400	90	6.75
3.78	3 50/64	0.39	3.82	3 53/64	3 60/64	FRSS300360	4	CSSS300400	90	7.08
3.80	3 51/64	0.40	3.83	3 53/64	3 60/64	FRSS300360	4	CSSS300400	90	7.41
3.82	3 52/64	0.41	3.85	3 54/64	4	FRSS300400	4	CSSS300400	90	7.74
3.84	3 54/64	0.42	3.86	3 55/64	4	FRSS300400	4	CSSS300400	90	8.07
3.86	3 54/64	0.43	3.87	3 56/64	4	FRSS300400	4	CSSS300400	90	8.40
3.88	3 56/64	0.44	3.89	3 57/64	4 8/64	FRSS300408	4	CSSS300400	90	8.73
3.90	3 58/64	0.45	3.90	3 58/64	4 8/64	FRSS300408	4	CSSS300400	90	9.06
3.92	3 59/64	0.46	3.91	3 58/64	4 8/64	FRSS300408	4	CSSS300400	90	9.39
3.94	3 60/64	0.47	3.93	3 59/64	4 8/64	FRSS300408	–	–	90	9.72
3.96	3 61/64	0.48	3.94	3 60/64	4 8/64	FRSS300408	–	–	90	10.05
3.98	3 63/64	0.49	3.95	3 61/64	4 8/64	FRSS300408	–	–	90	10.38
4.00	4	0.50	3.96	3 62/64	4 16/64	FRSS300416	–	–	90	10.71

Current Paladin® Crimp Sleeve CSSS200302 has been replaced by CSSS200300.
Over 75 psi it is recommended using Insta-Lock™ in combination with banding coil.
*Using OD Measurement Method **Quality of final crimp not verified with die selections, listed closest standard die set

4 in. Chart B | Infinity™/Paladin®/Insta-Lock™

Insta-Lock™ 4 in. Crimp Chart*

For Infinity™/Paladin® Crimp Sleeves on Infinity™/Paladin® Hose

									Perma-Crimp™	
Hose OD	Hose OD 64ths	Wall	Crimp Diameter	Crimp Diameter 64ths	Ferrule ID	Ferrule Part #	Sleeve ID	Sleeve Part #	Die Set**	Setting
4.68	4 44/64	0.34	4.76	4 48/64	4 56/64	FRSS400456	5	CSSS400500	118	2.83
4.70	4 45/64	0.35	4.77	4 49/64	4 56/64	FRSS400456	5	CSSS400500	118	3.16
4.72	4 46/64	0.36	4.78	4 50/64	4 56/64	FRSS400456	5	CSSS400500	118	3.49
4.74	4 47/64	0.37	4.80	4 51/64	4 56/64	FRSS400456	5	CSSS400500	118	3.82
4.76	4 49/64	0.38	4.81	4 52/64	4 60/64	FRSS400460	5	CSSS400500	118	4.15
4.78	4 50/64	0.39	4.82	4 53/64	4 60/64	FRSS400460	5	CSSS400500	118	4.48
4.80	4 51/64	0.4	4.83	4 53/64	4 60/64	FRSS400460	5	CSSS400500	118	4.81
4.82	4 52/64	0.41	4.85	4 54/64	5	FRSS400500	5	CSSS400500	118	5.14
4.84	4 54/64	0.42	4.86	4 55/64	5	FRSS400500	5	CSSS400500	118	5.47
4.86	4 55/64	0.43	4.87	4 56/64	5	FRSS400500	5	CSSS400500	118	5.80
4.88	4 56/64	0.44	4.89	4 57/64	5 4/64	FRSS400504	5	CSSS400500	118	6.13
4.90	4 58/64	0.45	4.90	4 58/64	5 4/64	FRSS400504	5	CSSS400500	118	6.46
4.92	4 59/64	0.46	4.91	4 58/64	5 4/64	FRSS400504	5	CSSS400500	118	6.79
4.94	4 60/64	0.47	4.93	4 59/64	–	–	5	CSSS400500	118	7.12
4.96	4 61/64	0.48	4.94	4 60/64	–	–	5	CSSS400500	118	7.45

Current Paladin® Crimp Sleeve CSSS200302 has been replaced by CSSS200300.
Over 75 psi it is recommended using Insta-Lock™ in combination with banding coil.
*Using OD Measurement Method **Quality of final crimp not verified with die selections, listed closest standard die set

Chart C | Pressure Washer Hose

Crimp Chart for 1/4 in. Pressure Washer Hose

Perma-Crimp™

Hose Description	Hose Product Code	Hose ID (in.)	Non-Swivel Male NPTF Product Code	Swivel Male NPTF Product Code	Crimp Diameter (in.)	Die Set**	Approximate Setting
Black Neptune™ 3000	539-085-008	1/4	539-173-538-24000	539-173-538-23600	.665	16	0.89
Blue Neptune™ 3000	539-089-008	1/4	539-173-538-24000	539-173-538-23600	.665	16	0.89
Gray Neptune™ 3000	539-090-008	1/4	539-173-538-24000	539-173-538-23600	.665	16	0.89
Black Gauntlet® 3000	539-099-008	1/4	539-173-538-24000	539-173-538-23600	.665	16	0.89
Yellow Gauntlet® 3000	539-100-008	1/4	539-173-538-24000	539-173-538-23600	.665	16	0.89
Yellow Neptune™ 3000	539-104-008	1/4	539-173-538-24000	539-173-538-23600	.665	16	0.89
Black Neptune™ 3000	539-085-008	1/4	B2-NPM-04xx	B2-NPMX-04xx	0.670	16	1.02
Blue Neptune™ 3000	539-089-008	1/4	B2-NPM-04xx	B2-NPMX-04xx	0.670	16	1.02
Gray Neptune™ 3000	539-090-008	1/4	B2-NPM-04xx	B2-NPMX-04xx	0.670	16	1.02
Black Gauntlet® 3000	539-099-008	1/4	B2-NPM-04xx	B2-NPMX-04xx	0.670	16	1.02
Yellow Gauntlet® 3000	539-100-008	1/4	B2-NPM-04xx	B2-NPMX-04xx	0.670	16	1.02

The crimp diameter tolerance is +/- .005" and to be the full length of the ferrule. The recommended crimp diameters are only related to Continental hoses noted above, and the male NPTF fittings noted above. **Quality of final crimp not verified with die selections, listed closest standard die set

Crimp Chart for 3/8 in. Pressure Washer Hose

Perma-Crimp™

Hose Description	Hose Product Code	Hose ID (in.)	Non-Swivel Male NPTF Product Code	Swivel Male NPTF Product Code	Crimp Diameter (in.)	Die Set**	Approximate Setting
Black Neptune™ 3000	539-085-012	3/8	539-173-538-22800	539-173-538-22900	.840	19	2.34
Blue Neptune™ 3000	539-089-012	3/8	539-173-538-22800	539-173-538-22900	.840	19	2.34
Black Gauntlet® 3000	539-099-012	3/8	539-173-538-22800	539-173-538-22900	.840	19	2.34
Yellow Gauntlet® 3000	539-100-012	3/8	539-173-538-22800	539-173-538-22900	.840	19	2.34
Yellow Neptune™ 3000	539-104-012	3/8	539-173-538-22800	539-173-538-22900	.840	19	2.34
Green Neptune™ 3000	539-154-012	3/8	539-173-538-22800	539-173-538-22900	.840	19	2.34
Yellow Fortress® 3000	539-400-012	3/8	539-173-538-22800	539-173-538-22900	.840	19	2.34
Yellow Galvanator® 3000	539-200-012	3/8	539-173-538-22800	539-173-538-22900	.840	19	2.34
Black Neptune™ 3000	539-085-012	3/8	B2-NPM-06xx	B2-NPMX-06xx	0.812	19	1.62
Blue Neptune™ 3000	539-089-012	3/8	B2-NPM-06xx	B2-NPMX-06xx	0.812	19	1.62
Black Gauntlet® 3000	539-099-012	3/8	B2-NPM-06xx	B2-NPMX-06xx	0.812	19	1.62
Yellow Gauntlet® 3000	539-100-012	3/8	B2-NPM-06xx	B2-NPMX-06xx	0.812	19	1.62
Yellow Neptune™ 3000	539-104-012	3/8	B2-NPM-06xx	B2-NPMX-06xx	0.812	19	1.62
Green Neptune™ 3000	539-154-012	3/8	B2-NPM-06xx	B2-NPMX-06xx	0.812	19	1.62
Yellow Fortress® 3000	539-400-012	3/8	B2-NPM-06xx	B2-NPMX-06xx	0.812	19	1.62
Yellow Galvanator® 3000	539-200-012	3/8	B2-NPM-06xx	B2-NPMX-06xx	0.812	19	1.62
Black Neptune™ 4001	539-261-012	3/8	539-173-538-22800	539-173-538-22900	.815	19	1.70
Gray Neptune™ 4001	539-262-012	3/8	539-173-538-22800	539-173-538-22900	.815	19	1.70

Crimp chart for 3/8 in. pressure washer hose continued on next page



Chart C | Pressure Washer Hose

Crimp Chart for 3/8 in. Pressure Washer Hose (continued)

Perma-Crimp™

Hose Description	Hose Product Code	Hose ID (in.)	Non-Swivel Male NPTF Product Code	Swivel Male NPTF Product Code	Crimp Diameter (in.)	Die Set**	Approximate Setting
Blue Neptune™ 4001	539-265-012	3/8	539-173-538-22800	539-173-538-22900	0.815	19	1.70
Yellow Neptune™ 4001	539-266-012	3/8	539-173-538-22800	539-173-538-22900	0.815	19	1.70
Black Neptune™ 4500	539-091-012	3/8	539-173-538-22800	539-173-538-22900	0.840	19	2.34
Red Neptune™ 4500	539-111-012	3/8	539-173-538-22800	539-173-538-22900	0.840	19	2.34
Yellow Gauntlet® 4500	539-120-012	3/8	539-173-538-22800	539-173-538-22900	0.840	19	2.34
Black Gauntlet® 4500	539-122-012	3/8	539-173-538-22800	539-173-538-22900	0.840	19	2.34
Blue Neptune™ 4500	539-124-012	3/8	539-173-538-22800	539-173-538-22900	0.840	19	2.34
Black Neptune™ 6000	539-149-012	3/8	539-173-538-22800	539-173-538-22900	0.850	19	2.59

The crimp diameter tolerance is +/- .005" and to be the full length of the ferrule. The recommended crimp diameters are only related to Continental hoses noted above, and the male NPTF fittings noted above. **Quality of final crimp not verified with die selections, listed closest standard die set

Crimp Chart for 1/2 in. Pressure Washer Hose (with Skive-to-Wire)

Perma-Crimp™

Hose Description	Hose Product Code	Hose ID (in.)	Non-Swivel Male NPT Anchor Product Code*	Swivel Male NPT Anchor Product Code*	Skive Length (in.)	Crimp Diameter (in.)	Die Set**	Approximate Setting
Black Neptune™ 3000	539-085-016	1/2	955-10-0808	955-11-0808	15/16	0.925	23	0.50
Blue Neptune™ 3000	539-089-016	1/2	955-10-0808	955-11-0808	15/16	0.925	23	0.50
Black Gauntlet® 4500	539-122-016	1/2	955-10-0808	955-11-0808	15/16	0.925	23	0.50
Black Gauntlet® 3000	539-099-016	1/2	955-10-0808	955-11-0808	15/16	0.925	23	0.50
Yellow Gauntlet® 3000	539-100-016	1/2	955-10-0808	955-11-0808	15/16	0.925	23	0.50
Galvanator® 3000	539-200-016	1/2	955-10-0808	955-11-0808	15/16	0.925	23	0.50
Black Neptune™ 4500	539-091-016	1/2	955-10-0808	955-11-0808	15/16	0.925	23	0.50
Blue Neptune™ 4500	539-124-016	1/2	955-10-0808	955-11-0808	15/16	0.925	23	0.50
Blue Neptune™ 3000	539-089-016	1/2	B2-NPM-08xx	B2-NPMX-08xx	N/A	0.920	23	0.37
Yellow Fortress™ 3000	539-400-016	1/2	B2-NPM-08xx	B2-NPMX-08xx	N/A	0.920	23	0.37
Yellow Gauntlet® 3000	539-100-016	1/2	B2-NPM-08xx	B2-NPMX-08xx	N/A	0.920	23	0.37
Black Neptune™ 3000	539-085-016	1/2	B2-NPM-08xx	B2-NPMX-08xx	N/A	0.920	23	0.37
Black Gauntlet® 3000	539-099-016	1/2	B2-NPM-08xx	B2-NPMX-08xx	N/A	0.920	23	0.37

**Quality of final crimp not verified with die selections, listed closest standard die set

Crimp Chart for 3/8 in. SpiraFlow® (with Skive-to-OD)

Perma-Crimp™

Hose Description	Hose Product Code	Hose ID (in.)	Non-Swivel Male NPTF Product Code	Swivel Male NPTF Product Code	Skive Length (in.)	Skive Diameter (in.)	Crimp Diameter (in.)	Die Set**	Approximate Setting
Black SpiraFlow®	539-185-012	3/8	539-173-538-22800	539-173-538-22900	7/8	.690	0.815	19	1.70
Blue SpiraFlow®	539-186-012	3/8	539-173-538-22800	539-173-538-22900	7/8	.690	0.815	19	1.70
Gray SpiraFlow®	539-187-012	3/8	539-173-538-22800	539-173-538-22900	7/8	.690*	0.815	19	1.70

**Quality of final crimp not verified with die selections, listed closest standard die set

Crimp Chart for 3/8 in. and 1/2 in. Whitewater® (with Skive-to-Wire)

Perma-Crimp™

Hose Description	Hose Product Code	Hose ID (in.)	Non-Swivel Male NPT Anchor Product Code*	Skive Length (in.)	Crimp Diameter (in.)	Die Set**	Approximate Setting
Black Whitewater®	539-095-012	3/8	955-10-0606	15/16	0.800	19	1.32
Red Whitewater®	539-110-012	3/8	955-10-0606	15/16	0.800	19	1.32
Black Whitewater®	539-095-016	1/2	955-10-0808	15/16	0.925	23	0.50
Red Whitewater®	539-110-016	1/2	955-10-0808	15/16	0.925	23	0.50

*Fittings require skiving to the wire. The crimp diameter tolerance is +/- .005" and to be the full length of the ferrule. The recommended crimp diameters are only related to Continental hoses noted above and the male fittings noted above. **Quality of final crimp not verified with die selections, listed closest standard die set

Chart D | Air & Multipurpose

Frontier						Uni-Crimp™		
PSI	PSI	PSI	Hose ID (in.)	Male Rigid NPT Stem***	Ferrule	Crimp Diameter** (in.)	Die Set†	Approximate Setting
200	N/A	N/A	3/16	UC-NPM-03XX	UCF2-03	0.636	14	2.15
200	250	300	1/4	UC-NPM-04XX	UCF2-04	0.720	16	2.29
200	250	N/A	5/16	UC-NPM-05XX	UCF2-05	0.750	19	0.05
200	250	300	3/8	UC-NPM-06XX	UCF2-06	0.835	19	3.35
200	250	300	1/2	UC-NPM-08XX	UCF2-08	1.040	23	3.40
200	250	300	5/8	UC-NPM-10XX	UCF2-10	1.190	27	3.22
200	250	300	3/4	UC-NPM-12XX	UCF2-12	1.350	31	3.29
200	250	300	1.0	UC-NPM-16XX	UCF6-16	1.670	41	1.42
200	N/A	N/A	1.25	UC-NPM-20XX	UCF6-20	1.820	45	1.23
200	N/A	N/A	1.5	UC-NPM-24XX	UCF6-24	2.100	50	3.34
200	N/A	N/A	2.0	UC-NPM-32XX	UCF6-32	2.650	62	5.30

Ortac®						Uni-Crimp™		
PSI	PSI	PSI	Hose ID (in.)	Male Rigid NPT Stem***	Ferrule	Crimp Diameter** (in.)	Die Set†	Approximate Setting
N/A	300	N/A	3/16	UC-NPM-03XX	UCF2-03	0.636	14	2.15
250	N/A	N/A	1/4	UC-NPM-04XX	UCF2-04	0.720	16	2.29
N/A	300	D*	1/4	UC-NPM-04XX	UCF6-04	0.710	16	2.03
250	300	400	5/16	UC-NPM-05XX	UCF6-05	0.800	19	1.32
250	300	400	3/8	UC-NPM-06XX	UCF6-06	0.8785	19	3.31
250	300	400	1/2	UC-NPM-08XX	UCF6-08	0.945	23	1.00
250	300	N/A	5/8	UC-NPM-10XX	UCF6-10	1.160	27	2.46
250	300	400	3/4	UC-NPM-12XX	UCF6-12	1.285	31	1.64
250	300	400	1.0	UC-NPM-16XX	UCF6-16	1.670	41	1.42
250	300	N/A	1.25	UC-NPM-20XX	UCF6-20	1.840	45	1.73
250	300	N/A	1.5	UC-NPM-24XX	UCF6-24	2.170	50	5.05
D*	N/A	N/A	2.0	UC-NPM-32XX	UCF6-32	N/A	N/A	N/A

*In development
 **The crimp diameter tolerance is +/- .005" and to be the full length of the ferrule.
 ***Listed crimp specifications are also valid for all available types of UC stem ends and threads.
 The recommended crimp diameters are only related to Continental hoses noted above.
 †Quality of final crimp not verified with die selections, listed closest standard die set

Chart D | Air & Multipurpose

Variflex™						Uni-Crimp™		
PSI	PSI	PSI	Hose ID (in.)	Male Rigid NPT Stem***	Ferrule	Crimp Diameter** (in.)	Die Set†	Approximate Setting
D*	N/A	N/A	3/16	UC-NPM-03XX	UCF2-03	0.636	14	2.15
200	N/A	300	1/4	UC-NPM-04XX	UCF2-04	0.720	16	2.29
200	N/A	300	5/16	UC-NPM-05XX	UCF6-05	0.800	19	1.32
200	N/A	300	3/8	UC-NPM-06XX	UCF6-06	0.8785	19	3.31
200	N/A	300	1/2	UC-NPM-08XX	UCF6-08	0.945	23	1.00
200	N/A	300	5/8	UC-NPM-10XX	UCF6-10	1.160	27	2.46
200	N/A	300	3/4	UC-NPM-12XX	UCF6-12	1.285	31	1.64
200	N/A	300	1.0	UC-NPM-16XX	UCF6-16	1.670	41	1.42
N/A	250	D*	1.25	UC-NPM-20XX	UCF6-20	1.840	45	1.73
N/A	250	D*	1.5	UC-NPM-24XX	UCF6-24	2.170	50	5.12
N/A	N/A	D*	2.0	UC-NPM-32XX	UCF6-32	N/A	N/A	N/A

Gorilla®						Uni-Crimp™	
PSI	Hose ID (in.)	Male Rigid NPT Stem***	Ferrule	Crimp Diameter** (in.)	Die Set†	Approximate Setting	
500	1/4	UC-NPM-04XX	UCF6-04	0.710	16	2.03	
500	3/8	UC-NPM-06XX	UCF6-06	0.8785	19	3.31	
500	1/2	UC-NPM-08XX	UCF6-08	0.945	23	1.00	
500	5/8	UC-NPM-10XX	UCF6-10	1.160	27	2.46	
500	3/4	UC-NPM-12XX	UCF6-12	1.285	31	1.64	
500	1.0	UC-NPM-16XX	UCF6-16	1.660	41	1.16	
500	1.25	UC-NPM-20XX	UCF6-20	1.844	45	1.84	
500	1.5	UC-NPM-24XX	UCF6-24	2.170	50	5.12	
500	2.0	UC-NPM-32XX	UCF6-32	2.740	69	0.60	

*In development
 **The crimp diameter tolerance is +/- .005" and to be the full length of the ferrule.
 ***Listed crimp specifications are also valid for all available types of UC stem ends and threads.
 The recommended crimp diameters are only related to Continental hoses noted above.
 †Quality of final crimp not verified with die selections, listed closest standard die set

Chart D | Air & Multipurpose

Gorilla® Couplamatic Vari-Crimp™ Couplings

PSI	Size	Hose Product Code	Fitting	Ferrule & Coupling Stem Length (in.)	Finn Power Crimper	
					Die Set***	Crimp OD (in.)
500	1/4"	569-035-064	P/N 403V	16-19	16mm	0.630
500	3/8"	569-035-095	P/N 603V	19-23	19mm	0.795
500	1/2"	569-035-127	P/N 803V	23-27	23mm	0.940
500	5/8"	569-035-159	P/N 1003V	27-31	27mm	1.105
500	3/4"	569-035-191	P/N 1203V	27-31	27mm	1.210
500	1.0"	569-035-254	P/N 1600V	36-41	36mm	1.500
500	1 1/4"	569-035-318	P/N 2000V	41-47	41mm	1.850
500	1 1/2"	539-035-381	N/A	54-61	N/A	N/A

Recommended Crimp Diameter for Mine Spray Hoses

ID	Continental Hydraulic Fitting Family	Crimp OD (in.)	Perma-Crimp™	
			Die Set***	Approximate Setting
3/4"	B2	1.265"	31	1.13
1"	B2	1.665"	41	1.29
1-1/4"	S4	1.935"	45	4.15
1-1/2"	S4	2.225"	56	0.52

Super Ortac®

ID	Continental Hydraulic Fitting Family	Crimp OD (in.)	Perma-Crimp™	
			Die Set***	Approximate Setting
3/4"	B2	1.265"	31	1.13
1"	B2	1.665"	41	1.29
1-1/4"	S4	1.980"	50	0.29
1-1/2"	S4	2.225"	56	0.52

Prospector™ Air

Hose ID	Product Code	Two Piece UC™ NPT Stem**	Fittings Ferrule	Crimp Diameter* (in.)	Uni-Crimp™	
					Die Set***	Approximate Setting (mm)
3/4"	536509024	UC-NPM-12XX	UCF6-12	1.320"	31	2.53
1"	536509032	UC-NPM-16XX	UCF6-16	1.675"	41	1.54

Prospector™ Plus Air

Hose ID	Product Code	Two Piece UC™ NPT Stem**	Fittings Ferrule	Crimp Diameter* (in.)	Uni-Crimp™	
					Die Set***	Approximate Setting (mm)
3/4"	536508024	UC-NPM-12XX	UCF6-12	1.320"	31	2.53
1"	536508032	UC-NPM-16XX	UCF6-16	1.675"	41	1.54

*The crimp diameter tolerance is +/- .005" and to be the full length of the ferrule.
 **Listed crimp specifications are also valid for all available types of UC stem ends and threads.
 ***Quality of final crimp not verified with die selections, listed closest standard die set



Chart E | Steam Hose

Recommended Over-the-Cover Crimp Diameters for Continental Branded Steam Hose

Hose Description	Hose Product Code	Hose ID	Campbell Female Ground Joint Female NPT Spud Low Profile Nut	Campbell Female Ground Joint Female NPT Spud Wing Nut	Campbell Male NPT	Campbell Male NPT Swivel	Female Spud	Crimp Diameter	Perma-Crimp™	
									Die Set**	Approximate Setting
Flexsteel® 250 Steam (Black, Red)	539-070-024	3/4"	RGJS-3V	GJS-3V	IMS-3V	IMS-3VSW	GFS-3	1.440"	34	2.60
Flexsteel® 250 Steam (Black, Red)	539-070-032	1"	RGJS-4V	GJS-4V	IMS-4V	IMS-4VSW	GFS-4	1.925"	45	3.90
Flexsteel® 250 EPDM-20 (Red)	539-486-024	3/4"	RGJF-3V	GJF-3V	IMS-3V	IMS-3VSW	GFS-3	1.420"	34	2.07
Flexsteel® 250 CB Extreme Crimp Steam (Black, Red)	539-870-024	3/4"	RGJF-3V	GJF-3V	IMS-3V	IMS-3VSW	GFS-3	1.430"	34	2.32
Flexsteel® 250 Steam Wrapped (Red)	539-476-016	1/2"	N/A	GJS-2V	IMS-2V	N/A	GFS-2	1.220"	27	3.99
Flexsteel® 250 Steam Wrapped (Black, Red)	539-470-024	3/4"	RGJS-3V	GJS-3V	IMS-3V	IMS-3VSW	GFS-3	1.440"	34	2.58
Flexsteel® 250 Steam Wrapped (Black, Red)	539-470-032	1"	RGJS-4V	GJS-4V	IMS-4V	IMS-4VSW	GFS-4	1.900"	45	3.26
Flexsteel® 250 Steam Wrapped (Black, Red)	559-201-510	2"	RGJS-8V	GJS-8V	IMS-8V	-	-	2.920"	74	0.17
Flexsteel® 250 ORS Steam	539-098-024	3/4"	RGJS-3V	GJS-3V	IMS-3V	IMS-3VSW	GFS-3	1.430"	34	2.32

Contact Campbell Fittings to purchase crimp-on steam hose fittings. The fitting part numbers are Campbell Fitting part numbers. The tolerance for the crimp diameters is +/- .005". Crimp the full length of the ferrule. The recommended crimp diameters are listed in the table above. Assemblies must meet the electrical resistance test requirements as specified in section 5.5 of the NAHAD Hose Assembly Guidelines or as specified in the ARPM Hose Tech Bulletin IP-11.
 **Quality of final crimp not verified with die selections, listed closest standard die set.

Chart F | DEF Dispensing Hose

Crimp Chart for 3/4 in. DEF Dispensing

Size	Hose Part #	Stem Part #	Stem Description	Ferrule Part #	Crimp OD (in.)
3/4"	532-027-024	53217353232900	SS, 3/4" Male NPT	53217353233200	1.220
3/4"	532-027-024	53217353233000	SS, 3/4" Male BSPP	53217353233200	1.220
3/4"	532-027-024	53217353233100	SS, 1" Female BSPP	53217353233200	1.220

The crimp diameter tolerance is +/- .005" and to be the full length of the ferrule. Any company who installs a fitting on Continental DEF hose takes responsibility for correct fitting installation, hose/fitting compatibility and grounding. This recommended crimp OD is only for the fittings above on Continental DEF hose sold and manufactured by Continental to be used specifically for DEF dispensing. The company installing the fitting must develop its own proper installation and quality control procedures. The installer must test and verify hose/fitting compatibility and ensure proper grounding. If requested, Continental will test coupled assemblies and report the test results back to the company who installed the fittings.

Chart G | Hydrocarbon Drain Hose

Recommended Over-the-Cover Crimp Diameter for Continental Branded Hydrocarbon Drain Hose

Hose Description	Hose Product Code	Hose ID	Hydraulic Fitting Family	Crimp Diameter	Die Set**	Approximate Setting
Hydrocarbon Drain Hose	547-819-024	3/4"	B2-xxx-12xx	1.272"	31	1.31

*The crimp diameter tolerance is +/- .005" and to be the full length of the ferrule.
 **Quality of final crimp not verified with die selections, listed closest standard die set.



Chart H | Velocity® Water S&D Hose

Crimp Chart for 1½" Velocity® Water S&D Hose

Wall Thickness		Hose OD		Sleeve Selection	Crimp Diameter		
in.	mm	in.	mm		in.	in.	mm
0.203	5.16	1 58/64	48.4	SxS150160S	1.933	1 60/64	49.10
0.211	5.36	1 59/64	48.8	SxS150160S	1.945	1 60/64	49.40
0.219	5.56	1 60/64	49.2	SxS150200S	1.957	1 61/64	49.71
0.227	5.75	1 61/64	49.6	SxS150200S	1.970	1 62/64	50.04
0.234	5.95	1 62/64	50.0	SxS150200S	1.982	1 63/64	50.34
0.242	6.15	1 63/64	50.4	SxS150200S	1.994	2	50.65
0.250	6.35	2	50.8	SxS150204S	2.007	2	50.98
0.258	6.55	2 1/64	51.2	SxS150204S	2.019	2 1/64	51.28
0.266	6.75	2 2/64	51.6	SxS150204S	2.031	2 2/64	51.59
0.273	6.95	2 3/64	52.0	SxS150204S	2.044	2 3/64	51.92
0.281	7.14	2 4/64	52.4	SxS150208S	2.056	2 4/64	52.22
0.289	7.34	2 5/64	52.8	SxS150208S	2.068	2 4/64	52.53
0.297	7.54	2 6/64	53.2	SxS150208S	2.081	2 5/64	52.86
0.305	7.74	2 7/64	53.6	SxS150208S	2.093	2 6/64	53.16
0.313	7.94	2 8/64	54.0	SxS150212S	2.105	2 7/64	53.47
0.320	8.14	2 9/64	54.4	SxS150212S	2.118	2 8/64	53.80

Crimp Chart for 2" Velocity® Water S&D Hose

Wall Thickness		Hose OD		Sleeve Selection	Crimp Diameter		
in.	mm	in.	mm		in.	in.	mm
0.203	5.16	2 26/64	61.1	SxS200228S	2.433	2 28/64	61.80
0.211	5.36	2 27/64	61.5	SxS200228S	2.445	2 28/64	62.10
0.219	5.56	2 28/64	61.9	SxS200232S	2.457	2 29/64	62.41
0.227	5.75	2 29/64	62.3	SxS200232S	2.470	2 30/64	62.74
0.234	5.95	2 30/64	62.7	SxS200232S	2.482	2 31/64	63.04
0.242	6.15	2 31/64	63.1	SxS200232S	2.494	2 32/64	63.35
0.250	6.35	2 32/64	63.5	SxS200236S	2.507	2 32/64	63.68
0.258	6.55	2 33/64	63.9	SxS200236S	2.519	2 33/64	63.98
0.266	6.75	2 34/64	64.3	SxS200236S	2.531	2 34/64	64.29
0.273	6.95	2 35/64	64.7	SxS200236S	2.544	2 35/64	64.62
0.281	7.14	2 36/64	65.1	SxS200240S	2.556	2 36/64	64.92
0.289	7.34	2 37/64	65.5	SxS200240S	2.568	2 36/64	65.23
0.297	7.54	2 38/64	65.9	SxS200240S	2.581	2 37/64	65.56
0.305	7.74	2 39/64	66.3	SxS200240S	2.593	2 38/64	65.86
0.313	7.94	2 40/64	66.7	SxS200244S	2.605	2 39/64	66.17
0.320	8.14	2 41/64	67.1	SxS200244S	2.618	2 40/64	66.50

Chart H | Velocity® Water S&D Hose

Crimp Chart for 3" Velocity® Water S&D Hose

Wall Thickness		Hose OD		Sleeve Selection	Crimp Diameter		
in.	mm	in.	mm		in.	in.	mm
0.297	7.54	3 38/64	91.3	SxS300340S	3.627	3 40/64	92.13
0.305	7.74	3 39/64	91.7	SxS300340S	3.639	3 41/64	92.43
0.313	7.94	3 40/64	92.1	SxS300344S	3.651	3 42/64	92.74
0.320	8.14	3 41/64	92.5	SxS300344S	3.664	3 42/64	93.07
0.328	8.33	3 42/64	92.9	SxS300344S	3.676	3 43/64	93.37
0.336	8.53	3 43/64	93.3	SxS300344S	3.688	3 44/64	93.68
0.344	8.73	3 44/64	93.7	SxS300348S	3.701	3 45/64	94.01
0.352	8.93	3 45/64	94.1	SxS300348S	3.713	3 46/64	94.31
0.359	9.13	3 46/64	94.5	SxS300348S	3.725	3 46/64	94.62
0.367	9.33	3 47/64	94.9	SxS300348S	3.738	3 47/64	94.95
0.375	9.53	3 48/64	95.3	SxS300352S	3.750	3 48/64	95.25
0.383	9.72	3 49/64	95.6	SxS300352S	3.763	3 49/64	95.58
0.391	9.92	3 50/64	96.0	SxS300352S	3.775	3 50/64	95.89
0.398	10.12	3 51/64	96.4	SxS300352S	3.787	3 50/64	96.19
0.406	10.32	3 52/64	96.8	SxS300356S	3.800	3 51/64	96.52
0.414	10.52	3 53/64	97.2	SxS300356S	3.812	3 52/64	96.82
0.422	10.72	3 54/64	97.6	SxS300356S	3.824	3 53/64	97.13

Crimp Chart for 4" Velocity® Water S&D Hose

Wall Thickness		Hose OD		Sleeve Selection	Crimp Diameter		
in.	mm	in.	mm		in.	in.	mm
0.297	7.54	4 38/64	116.7	SxS400440S	4.627	4 40/64	117.53
0.305	7.74	4 39/64	117.1	SxS400440S	4.639	4 41/64	117.83
0.313	7.94	4 40/64	117.5	SxS400444S	4.651	4 42/64	118.14
0.320	8.14	4 41/64	117.9	SxS400444S	4.664	4 42/64	118.47
0.328	8.33	4 42/64	118.3	SxS400444S	4.676	4 43/64	118.77
0.336	8.53	4 43/64	118.7	SxS400444S	4.688	4 44/64	119.08
0.344	8.73	4 44/64	119.1	SxS400448S	4.701	4 45/64	119.41
0.352	8.93	4 45/64	119.5	SxS400448S	4.713	4 46/64	119.71
0.359	9.13	4 46/64	119.9	SxS400448S	4.725	4 46/64	120.02
0.367	9.33	4 47/64	120.3	SxS400448S	4.738	4 47/64	120.35
0.375	9.53	4 48/64	120.7	SxS400452S	4.750	4 48/64	120.65
0.383	9.72	4 49/64	121.0	SxS400452S	4.763	4 49/64	120.98
0.391	9.92	4 50/64	121.4	SxS400452S	4.775	4 50/64	121.29
0.398	10.12	4 51/64	121.8	SxS400452S	4.787	4 50/64	121.59
0.406	10.32	4 52/64	122.2	SxS400456S	4.800	4 51/64	121.92
0.414	10.52	4 53/64	122.6	SxS400456S	4.812	4 52/64	122.22
0.422	10.72	4 54/64	123.0	SxS400456S	4.824	4 53/64	122.53

Chart H | Velocity® Water S&D Hose

Crimp Chart for 6" Velocity® Water S&D Hose

Wall Thickness		Hose OD		Sleeve Selection	Crimp Diameter		
in.	mm	in.	mm		in.	in.	mm
0.516	13.10	7 2/64	178.6	SxS600708	7.042	7 3/64	178.87
0.523	13.30	7 3/64	179.0	SxS600708	7.055	7 4/64	179.20
0.531	13.49	7 4/64	179.4	SxS600708	7.067	7 4/64	179.50
0.539	13.69	7 5/64	179.8	SxS600708	7.079	7 5/64	179.81
0.547	13.89	7 6/64	180.2	SxS600708	7.092	7 6/64	180.14
0.555	14.09	7 7/64	180.6	SxS600708	7.104	7 7/64	180.44
0.563	14.29	7 8/64	181.0	SxS600716	7.116	7 7/64	180.75
0.570	14.49	7 9/64	181.4	SxS600716	7.129	7 8/64	181.08
0.578	14.68	7 10/64	181.8	SxS600716	7.141	7 9/64	181.38
0.586	14.88	7 11/64	182.2	SxS600716	7.153	7 10/64	181.69
0.594	15.08	7 12/64	182.6	SxS600716	7.166	7 11/64	182.02
0.602	15.28	7 13/64	183.0	SxS600716	7.178	7 11/64	182.32
0.609	15.48	7 14/64	183.4	SxS600716	7.190	7 12/64	182.63
0.617	15.68	7 15/64	183.8	SxS600716	7.203	7 13/64	182.96
0.625	15.88	7 16/64	184.2	SxS600724	7.215	7 14/64	183.26
0.633	16.07	7 17/64	184.5	SxS600724	7.228	7 15/64	183.59
0.641	16.27	7 18/64	184.9	SxS600724	7.240	7 15/64	183.90

Crimp Chart for 8" Velocity® Water S&D Hose

Wall Thickness		Hose OD		Sleeve Selection	Crimp Diameter		
in.	mm	in.	mm		in.	in.	mm
0.531	13.49	9 4/64	230.2	SPS800916	9.067	9 4/64	230.30
0.539	13.69	9 5/64	230.6	SPS800916	9.079	9 5/64	230.61
0.547	13.89	9 6/64	231.0	SPS800916	9.092	9 6/64	230.94
0.555	14.09	9 7/64	231.4	SPS800916	9.104	9 7/64	231.24
0.563	14.29	9 8/64	231.8	SPS800916	9.116	9 7/64	231.55
0.570	14.49	9 9/64	232.2	SPS800916	9.129	9 8/64	231.88
0.578	14.68	9 10/64	232.6	SPS800916	9.141	9 9/64	232.18
0.586	14.88	9 11/64	233.0	SPS800916	9.153	9 10/64	232.49
0.594	15.08	9 12/64	233.4	SPS800916	9.166	9 11/64	232.82
0.602	15.28	9 13/64	233.8	SPS800916	9.178	9 11/64	233.12
0.609	15.48	9 14/64	234.2	SPS800916	9.190	9 12/64	233.43
0.617	15.68	9 15/64	234.6	SPS800916	9.203	9 13/64	233.76
0.625	15.88	9 16/64	235.0	SPS800932	9.215	9 14/64	234.06
0.633	16.07	9 17/64	235.3	SPS800932	9.228	9 15/64	234.39
0.641	16.27	9 18/64	235.7	SPS800932	9.240	9 15/64	234.70
0.648	16.47	9 19/64	236.1	SPS800932	9.252	9 16/64	235.00
0.656	16.67	9 20/64	236.5	SPS800932	9.265	9 17/64	235.33
0.664	16.87	9 21/64	236.9	SPS800932	9.277	9 18/64	235.64

Dixon Part Numbers Sanitary Style Crimp Stems

Clamp End x Hose Shank

Size	316 Stainless Steel Part #
1"	CSSR100-3A
1½"	CSSR150-3A
2"	CSSR200-3A
2½"	CSSR250
3"	CSSR300-3A
4"	CSSR400

Bevel Seat End x Hose Shank

Size	Nut Used	316 Stainless Steel Part #
1½"	IXAN24	CBSR150
2"	IXAN32	CBSR200
3"	IXAN300	CBSR300
4"	IXAN64	CBSR400

Female I-Line End x Hose Shank

Size	316 Stainless Steel Part #
1½"	CILR150
2"	CILR200
3"	CILR300
4"	CILR400

Tube Weld End x Hose Shank

Size	316 Stainless Steel Part #
1½"	CTER150
2"	CTER200
3"	CTER300
4"	CTER400

Note: Dixon Sanitary Crimp Stems are only to be used with Dixon Sanitary Stainless Steel Crimp Ferrules.

Table F-A

1.0" Hose Crimp Chart

Measured Hose Wall Thickness Min. / Max.	Measured Hose OD Min. / Max.	Measured Hose OD In Closest 64ths	Finished Crimp Diameter Decimal	Finished Crimp Diameter Closest 64ths	Crimp Die	Setting	Dixon Sanitary Stainless Steel Crimp Ferrules
0.168 / 0.176	1.337 / 1.352	1 22/64	1.514	1 33/64	34	4.46	Contact Customer Service
0.176 / 0.184	1.353 / 1.367	1 23/64	1.526	1 34/64	34	4.47	Contact Customer Service
0.184 / 0.191	1.368 / 1.383	1 24/64	1.538	1 34/64	34	5.07	F16G-1453
0.192 / 0.199	1.384 / 1.980	1 25/64	1.550	1 35/64	34	5.38	F16G-1453
0.200 / 0.207	1.339 / 1.414	1 26/64	1.562	1 36/64	34	5.68	F16G-1453
0.208 / 0.215	1.415 / 1.430	1 27/64	1.574	1 37/64	34	5.99	F16G-1453
0.215 / 0.223	1.431 / 1.445	1 28/64	1.586	1 38/64	34	6.29	F16G-1500
0.223 / 0.230	1.446 / 1.461	1 29/64	1.598	1 38/64	34	6.60	F16G-1500
0.231 / 0.238	1.462 / 1.477	1 30/64	1.610	1 39/64	34	6.91	F16G-1500
0.239 / 0.246	1.478 / 1.492	1 31/64	1.623	1 40/64	34	7.21	F16G-1500
0.247 / 0.254	1.493 / 1.508	1 32/64	1.635	1 41/64	34	7.52	F16G-1547
0.254 / 0.262	1.509 / 1.523	1 33/64	1.647	1 41/64	34	7.82	F16G-1547
0.262 / 0.270	1.524 / 1.539	1 34/64	1.659	1 42/64	34	8.13	F16G-1547
0.270 / 0.277	1.550 / 1.555	1 35/64	1.671	1 43/64	41	1.43	F16G-1594
0.278 / 0.285	1.556 / 1.570	1 36/64	1.683	1 44/64	41	1.74	F16G-1594
0.286 / 0.293	1.557 / 1.586	1 37/64	1.695	1 44/64	41	2.05	F16G-1594
0.293 / 0.301	1.587 / 1.602	1 38/64	1.707	1 45/64	41	2.35	F16G-1641
0.301 / 0.309	1.603 / 1.617	1 39/64	1.719	1 46/64	41	2.66	F16G-1641
0.309 / 0.316	1.618 / 1.633	1 40/64	1.731	1 47/64	41	2.96	F16G-1641
0.317 / 0.324	1.634 / 1.648	1 41/64	1.743	1 48/64	41	3.27	-
0.325 / 0.332	1.649 / 1.664	1 42/64	1.755	1 48/64	41	3.57	-
0.333 / 0.340	1.665 / 1.680	1 43/64	1.767	1 49/64	41	3.88	-
0.340 / 0.348	1.681 / 1.695	1 44/64	1.779	1 50/64	41	4.18	-

Note: Refer to Recommended Crimp Chart Index Selection to validate if you are using the appropriate chart for the hose on hand. This chart refers to Dixon Sanitary Style Crimp Stems.

Table F-A

1.5" Hose Crimp Chart

Measured Hose Wall Thickness Min. / Max.	Measured Hose OD Min. / Max.	Measured Hose OD In Closest 64ths	Finished Crimp Diameter Decimal	Finished Crimp Diameter Closest 64ths	Crimp Die	Setting	Dixon Sanitary Stainless Steel Crimp Ferrules
0.168 / 0.176	1.837 / 1.852	1 54/64	2.014	2 1/64	45	6.14	Contact Customer Service
0.176 / 0.184	1.853 / 1.867	1 55/64	2.026	2 2/64	45	6.45	Contact Customer Service
0.184 / 0.191	1.868 / 1.883	1 56/64	2.038	2 2/64	45	6.76	Contact Customer Service
0.192 / 0.199	1.884 / 1.898	1 57/64	2.050	2 3/64	45	7.06	Contact Customer Service
0.200 / 0.207	1.899 / 1.914	1 58/64	2.062	2 4/64	45	7.37	F24G-1969
0.208 / 0.215	1.915 / 1.930	1 59/64	2.074	2 5/64	45	7.67	F24G-1969
0.215 / 0.223	1.913 / 1.945	1 60/64	2.086	2 5/64	45	7.98	F24G-1969
0.223 / 0.230	1.946 / 1.961	1 61/64	2.098	2 6/64	45	8.28	F24G-1969
0.231 / 0.238	1.962 / 1.977	1 62/64	2.110	2 7/64	50	3.59	F24G-2031
0.239 / 0.246	1.978 / 1.992	1 63/64	2.122	2 8/64	50	3.89	F24G-2031
0.247 / 0.254	1.993 / 2.008	2	2.134	2 9/64	50	4.20	F24G-2031
0.254 / 0.262	2.009 / 2.023	2 1/64	2.146	2 9/64	50	4.51	F24G-2031
0.262 / 0.270	2.024 / 2.039	2 2/64	2.158	2 10/64	50	4.81	F24G-2094
0.270 / 0.277	2.040 / 2.055	2 3/64	2.170	2 11/64	50	5.12	F24G-2094
0.278 / 0.285	2.056 / 2.070	2 4/64	2.182	2 12/64	50	5.42	F24G-2094
0.286 / 0.293	2.071 / 2.086	2 5/64	2.194	2 12/64	50	5.73	F24G-2094
0.293 / 0.301	2.087 / 2.102	2 6/64	2.206	2 13/64	50	6.03	F24G-2156
0.301 / 0.309	2.103 / 2.117	2 7/64	2.218	2 14/64	50	6.34	F24G-2156
0.309 / 0.316	2.118 / 2.133	2 8/64	2.230	2 15/64	50	6.64	F24G-2156
0.317 / 0.324	2.134 / 2.148	2 9/64	2.242	2 15/64	50	6.95	F24G-2156
0.325 / 0.332	2.149 / 2.164	2 10/64	2.254	2 16/64	56	1.26	F24G-2219
0.333 / 0.340	2.165 / 2.180	2 11/64	2.266	2 17/64	56	1.56	F24G-2219
0.340 / 0.348	2.181 / 2.195	2 12/64	2.278	2 18/64	56	1.87	F24G-2219
0.348 / 0.355	2.196 / 2.211	2 13/64	2.290	2 19/64	56	2.17	F24G-2219
0.356 / 0.363	2.212 / 2.227	2 14/64	2.302	2 19/64	56	2.48	F24G-2281
0.364 / 0.371	2.228 / 2.242	2 15/64	2.314	2 20/64	56	2.78	F24G-2281
0.372 / 0.379	2.243 / 2.258	2 16/64	2.326	2 21/64	56	3.09	F24G-2281
0.379 / 0.387	2.259 / 2.273	2 17/64	2.338	2 22/64	56	3.39	F24G-2281

Note: Refer to Recommended Crimp Chart Index Selection to validate if you are using the appropriate chart for the hose on hand. This chart refers to Dixon Sanitary Style Crimp Stems.

Table F-A

2.0" Hose Crimp Chart

Measured Hose Wall Thickness Min. / Max.	Measured Hose OD Min. / Max.	Measured Hose OD In Closest 64ths	Finished Crimp Diameter Decimal	Finished Crimp Diameter Closest 64ths	Crimp Die	Setting	Dixon Sanitary Stainless Steel Crimp Ferrules
0.200 / 0.207	2.339 / 2.414	2 26/64	2.560	2 36/64	62	3.03	Contact Customer Service
0.208 / 0.215	2.415 / 2.430	2 27/64	2.572	2 37/64	62	3.34	Contact Customer Service
0.215 / 0.223	2.431 / 2.445	2 28/64	2.584	2 37/64	62	3.64	Contact Customer Service
0.223 / 0.230	2.446 / 2.461	2 29/64	2.596	2 38/64	62	3.95	Contact Customer Service
0.231 / 0.238	2.462 / 2.477	2 30/64	2.608	2 39/64	62	4.25	F32G-2531
0.239 / 0.246	2.478 / 2.492	2 31/64	2.620	2 40/64	62	4.56	F32G-2531
0.274 / 0.254	2.493 / 2.508	2 32/64	2.632	2 40/64	62	4.86	F32G-2531
0.254 / 0.262	2.509 / 2.523	2 33/64	2.645	2 41/64	62	5.17	F32G-2531
0.262 / 0.270	2.524 / 2.539	2 34/64	2.657	2 42/64	62	5.48	F32G-2594
0.270 / 0.277	2.540 / 2.555	2 35/64	2.669	2 43/64	62	5.78	F32G-2594
0.278 / 0.285	2.556 / 2.570	2 36/64	2.681	2 44/64	62	6.09	F32G-2594
0.286 / 0.293	2.571 / 2.586	2 37/64	2.693	2 44/64	62	6.39	F32G-2594
0.293 / 0.301	2.587 / 2.602	2 38/64	2.705	2 45/64	62	6.70	F32G-2656
0.301 / 0.309	2.603 / 2.617	2 39/64	2.717	2 46/64	62	7.00	F32G-2656
0.309 / 0.316	2.618 / 2.633	2 40/64	2.729	2 47/64	62	7.31	F32G-2656
0.317 / 0.324	2.634 / 2.648	2 41/64	2.741	2 47/64	62	7.62	F32G-2656
0.325 / 0.332	2.649 / 2.664	2 42/64	2.753	2 48/64	62	7.92	F32G-2719
0.333 / 0.340	2.665 / 2.680	2 43/64	2.765	2 49/64	62	8.23	F32G-2719
0.340 / 0.348	2.681 / 2.695	2 44/64	2.777	2 50/64	62	8.53	F32G-2719
0.348 / 0.355	2.696 / 2.711	2 45/64	2.789	2 50/64	62	8.84	F32G-2719
0.356 / 0.363	2.712 / 2.727	2 46/64	2.801	2 51/64	69	2.14	Contact Customer Service
0.364 / 0.371	2.728 / 2.742	2 47/64	2.813	2 52/64	69	2.45	Contact Customer Service
0.372 / 0.379	2.743 / 2.758	2 48/64	2.825	2 53/64	69	2.75	Contact Customer Service
0.379 / 0.387	2.759 / 2.773	2 49/64	2.837	2 54/64	69	3.06	Contact Customer Service
0.387 / 0.395	2.774 / 2.789	2 50/64	2.849	2 54/64	69	3.37	Contact Customer Service
0.395 / 0.402	2.790 / 2.805	2 51/64	2.861	2 55/64	69	3.67	Contact Customer Service
0.403 / 0.410	2.806 / 2.820	2 52/64	2.873	2 56/64	69	3.98	F32G-2875
0.411 / 0.418	2.821 / 2.836	2 53/64	2.885	2 57/64	69	4.28	F32G-2875
0.418 / 0.426	2.837 / 2.852	2 54/64	2.897	2 57/64	69	4.59	F32G-2875
0.426 / 0.434	2.853 / 2.867	2 55/64	2.909	2 58/64	69	4.89	F32G-2875
0.434 / 0.441	2.868 / 2.883	2 56/64	2.921	2 59/64	69	5.20	F32G-2938
0.442 / 0.449	2.884 / 2.898	2 57/64	2.933	2 60/64	69	5.50	F32G-2938
0.450 / 0.457	2.899 / 2.914	2 58/64	2.946	2 60/64	69	5.81	F32G-2938
0.458 / 0.465	2.915 / 2.930	2 59/64	2.957	2 61/64	69	6.12	F32G-2938

Note: Refer to Recommended Crimp Chart Index Selection to validate if you are using the appropriate chart for the hose on hand. This chart refers to Dixon Sanitary Style Crimp Stems.

Table F-A

2.5" Hose Crimp Chart

Measured Hose Wall Thickness Min. / Max.	Measured Hose OD Min. / Max.	Measured Hose OD In Closest 64ths	Finished Crimp Diameter Decimal	Finished Crimp Diameter Closest 64ths	Crimp Die	Setting	Dixon Sanitary Stainless Steel Crimp Ferrules
0.200 / 0.207	2.899 / 2.914	2 58/64	3.062	3 4/64	74	3.77	Contact Customer Service
0.208 / 0.215	2.915 / 2.930	2 59/64	3.074	3 5/64	74	4.07	Contact Customer Service
0.215 / 0.223	2.931 / 2.945	2 60/64	3.086	3 5/64	74	3.38	Contact Customer Service
0.223 / 0.230	2.946 / 2.961	2 61/64	3.098	3 6/64	74	4.68	Contact Customer Service
0.231 / 0.238	2.962 / 2.977	2 62/64	3.110	3 7/64	74	4.99	Contact Customer Service
0.239 / 0.246	2.978 / 2.992	2 63/64	3.122	3 8/64	74	5.29	Contact Customer Service
0.247 / 0.254	2.993 / 3.008	3	3.134	3 9/64	78	1.60	F40G-3063
0.254 / 0.262	3.009 / 3.023	3 1/64	3.146	3 9/64	78	1.91	F40G-3063
0.262 / 0.270	3.024 / 3.039	3 2/64	3.158	3 10/64	78	2.21	F40G-3063
0.270 / 0.277	3.040 / 3.055	3 3/64	3.170	3 11/64	78	2.52	F40G-3063
0.278 / 0.285	3.056 / 3.070	3 4/64	3.182	3 12/64	78	2.82	F40G-3125
0.286 / 0.293	3.071 / 3.086	3 5/64	3.194	3 12/64	78	3.13	F40G-3125
0.293 / 0.301	3.087 / 3.102	3 6/64	3.206	3 13/64	78	3.43	F40G-3125
0.301 / 0.309	3.103 / 3.117	3 7/64	3.218	3 14/64	78	3.74	F40G-3125
0.309 / 0.316	3.118 / 3.133	3 8/64	3.230	3 15/64	78	4.04	F40G-3188
0.317 / 0.324	3.134 / 3.148	3 9/64	3.242	3 15/64	78	4.35	F40G-3188
0.325 / 0.332	3.149 / 3.164	3 10/64	3.254	3 16/64	78	4.66	F40G-3188
0.333 / 0.340	3.165 / 3.180	3 11/64	3.266	3 17/64	78	4.96	F40G-3188
0.340 / 0.348	3.181 / 3.195	3 12/64	3.278	3 18/64	78	5.27	F40G-3250
0.348 / 0.355	3.196 / 3.211	3 13/64	3.290	3 19/64	78	5.57	F40G-3250
0.356 / 0.363	3.212 / 3.227	3 14/64	3.302	3 19/64	78	5.88	F40G-3250
0.364 / 0.371	3.228 / 3.242	3 15/64	3.314	3 20/64	78	6.18	F40G-3250
0.372 / 0.379	3.243 / 3.258	3 16/64	3.326	3 21/64	78	6.49	F40G-3313
0.379 / 0.387	3.259 / 3.273	3 17/64	3.338	3 22/64	78	6.79	F40G-3313
0.387 / 0.395	3.274 / 3.289	3 18/64	3.350	3 22/64	78	7.10	F40G-3313
0.395 / 0.402	3.290 / 3.305	3 19/64	3.362	3 23/64	78	7.41	F40G-3313
0.403 / 0.410	3.306 / 3.320	3 20/64	3.374	3 24/64	78	7.71	F40G-3375
0.411 / 0.418	3.321 / 3.336	3 21/64	3.387	3 25/64	78	8.02	F40G-3375
0.418 / 0.426	3.337 / 3.352	3 22/64	3.399	3 26/64	78	8.32	F40G-3375
0.426 / 0.434	3.353 / 3.367	3 23/64	3.411	3 26/64	78	8.63	F40G-3375
0.434 / 0.441	3.368 / 3.383	3 24/64	3.423	3 27/64	86	0.93	Contact Customer Service
0.442 / 0.449	3.384 / 3.398	3 25/64	3.435	3 28/64	86	1.24	Contact Customer Service
0.450 / 0.457	3.399 / 3.414	3 26/64	3.447	3 29/64	86	1.55	Contact Customer Service
0.458 / 0.465	3.415 / 3.430	3 27/64	3.459	3 29/64	86	1.85	Contact Customer Service

Note: Refer to Recommended Crimp Chart Index Selection to validate if you are using the appropriate chart for the hose on hand. This chart refers to Dixon Sanitary Style Crimp Stems.

Table F-A

3.0" Hose Crimp Chart

Measured Hose Wall Thickness Min. / Max.	Measured Hose OD Min. / Max.	Measured Hose OD In Closest 64ths	Finished Crimp Diameter Decimal	Finished Crimp Diameter Closest 64ths	Crimp Die	Setting	Dixon Sanitary Stainless Steel Crimp Ferrules
0.262 / 0.270	3.524 / 3.539	3 34/64	3.657	3 42/64	92	0.89	–
0.270 / 0.277	3.540 / 3.555	3 35/64	3.669	3 43/64	92	1.20	–
0.278 / 0.285	3.556 / 3.570	3 36/64	3.681	3 44/64	92	1.50	F48G-3625
0.286 / 0.293	3.571 / 3.586	3 37/64	3.693	3 44/64	92	1.81	F48G-3625
0.293 / 0.301	3.587 / 3.602	3 38/64	3.705	3 45/64	92	2.12	F48G-3625
0.301 / 0.309	3.603 / 3.617	3 39/64	3.717	3 46/64	92	2.42	F48G-3625
0.309 / 0.316	3.618 / 3.633	3 40/64	3.729	3 47/64	92	2.73	F48G-3688
0.317 / 0.324	3.634 / 3.648	3 41/64	3.741	3 47/64	92	3.03	F48G-3688
0.325 / 0.332	3.649 / 3.664	3 42/64	3.753	3 48/64	92	3.34	F48G-3688
0.333 / 0.340	3.665 / 3.680	3 43/64	3.766	3 49/64	92	3.64	F48G-3688
0.340 / 0.348	3.681 / 3.695	3 44/64	3.778	3 50/64	92	3.95	F48G-3750
0.348 / 0.355	3.696 / 3.711	3 45/64	3.790	3 51/64	92	4.25	F48G-3750
0.356 / 0.363	3.712 / 3.727	3 46/64	3.802	3 51/64	92	4.56	F48G-3750
0.364 / 0.371	3.728 / 3.742	3 47/64	3.802	3 52/64	92	4.87	F48G-3750
0.372 / 0.379	3.743 / 3.758	3 48/64	3.826	3 53/64	96	1.17	F48G-3813
0.379 / 0.387	3.759 / 3.773	3 49/64	3.838	3 54/64	96	1.48	F48G-3813
0.387 / 0.395	3.774 / 3.789	3 50/64	3.850	3 54/64	96	1.78	F48G-3813
0.395 / 0.402	3.790 / 3.805	3 51/64	3.862	3 55/64	96	2.09	F48G-3813
0.403 / 0.410	3.806 / 3.820	3 52/64	3.874	3 56/64	96	2.39	F48G-3875
0.411 / 0.418	3.821 / 3.836	3 53/64	3.886	3 57/64	96	2.70	F48G-3875
0.418 / 0.426	3.837 / 3.852	3 54/64	3.898	3 57/64	96	3.01	F48G-3875
0.426 / 0.434	3.853 / 3.867	3 55/64	3.910	3 58/64	96	3.31	F48G-3875
0.434 / 0.441	3.868 / 3.883	3 56/64	3.922	3 59/64	96	3.62	F48G-3938
0.442 / 0.449	3.884 / 3.898	3 57/64	3.934	3 60/64	96	3.92	F48G-3938
0.450 / 0.457	3.899 / 3.914	3 58/64	3.946	3 61/64	96	4.23	F48G-3938
0.458 / 0.465	3.915 / 3.930	3 59/64	3.958	3 61/64	96	4.53	F48G-3938
0.465 / 0.473	3.931 / 3.945	3 60/64	3.970	3 62/64	96	4.84	Contact Customer Service
0.473 / 0.480	3.946 / 3.961	3 61/64	3.982	3 63/64	96	5.14	Contact Customer Service
0.481 / 0.488	3.962 / 3.977	3 62/64	3.994	4	96	5.45	Contact Customer Service
0.489 / 0.496	3.978 / 3.992	3 63/64	4.006	4	96	5.76	Contact Customer Service
0.497 / 0.504	3.993 / 4.008	4	4.018	4 1/64	100	2.06	Contact Customer Service
0.504 / 0.512	4.009 / 4.023	4 1/64	4.030	4 2/64	100	2.37	Contact Customer Service
0.512 / 0.520	4.024 / 4.039	4 2/64	4.042	4 3/64	100	2.67	Contact Customer Service
0.520 / 0.527	4.040 / 4.055	4 3/64	4.054	4 3/64	100	2.98	Contact Customer Service
0.528 / 0.535	4.056 / 4.070	4 4/64	4.066	4 4/64	100	3.28	F48G-4106
0.536 / 0.543	4.071 / 4.086	4 5/64	4.078	4 5/64	100	3.59	F48G-4106
0.543 / 0.551	4.087 / 4.102	4 6/64	4.090	4 6/64	100	3.89	F48G-4106
0.551 / 0.559	4.103 / 4.117	4 7/64	4.102	4 7/64	100	4.20	F48G-4106

Note: Refer to Recommended Crimp Chart Index Selection to validate if you are using the appropriate chart for the hose on hand. This chart refers to Dixon Sanitary Style Crimp Stems.

Table F-B

3.0" Hose Crimp Chart

Measured Hose Wall Thickness Min. / Max.	Measured Hose OD Min. / Max.	Measured Hose OD In Closest 64ths	Finished Crimp Diameter Decimal	Finished Crimp Diameter Closest 64ths	Crimp Die	Setting	Dixon Sanitary Stainless Steel Crimp Ferrules
0.340 / 0.348	3.681 / 3.695	3 44/64	3.812	3 52/64	92	4.83	F48G-3750
0.348 / 0.355	3.396 / 3.711	3 45/64	3.825	3 53/64	92	5.16	F48G-3750
0.356 / 0.363	3.712 / 3.727	3 46/64	3.838	3 54/64	92	5.48	F48G-3750
0.364 / 0.371	3.728 / 3.742	3 47/64	3.851	3 54/64	92	5.81	F48G-3750
0.372 / 0.379	3.743 / 3.758	3 48/64	3.864	3 55/64	96	2.13	F48G-3813
0.379 / 0.387	3.759 / 3.773	3 49/64	3.876	3 56/64	96	2.46	F48G-3813
0.387 / 0.395	3.774 / 3.789	3 50/64	3.889	3 57/64	96	2.79	F48G-3813
0.395 / 0.402	3.790 / 3.805	3 51/64	3.902	3 58/64	96	3.11	F48G-3813
0.403 / 0.410	3.806 / 3.820	3 52/64	3.915	3 59/64	96	3.44	F48G-3875
0.411 / 0.418	3.821 / 3.836	3 53/64	3.928	3 59/64	96	3.76	F48G-3875
0.418 / 0.426	3.837 / 3.852	3 54/64	3.940	3 60/64	96	4.06	F48G-3875
0.426 / 0.434	3.853 / 3.867	3 55/64	3.953	3 61/64	96	4.41	F48G-3875
0.434 / 0.441	3.868 / 3.883	3 56/64	3.966	3 62/64	96	4.74	F48G-3938
0.442 / 0.449	3.884 / 3.898	3 57/64	3.979	3 63/64	96	5.06	F48G-3938
0.450 / 0.457	3.899 / 3.914	3 58/64	3.992	3 63/64	96	5.39	F48G-3938
0.458 / 0.465	3.915 / 3.930	3 59/64	4.004	4	96	5.71	F48G-3938

Note: Refer to Recommended Crimp Chart Index Selection to validate if you are using the appropriate chart for the hose on hand. This chart refers to Dixon Sanitary Style Crimp Stems.

Table F-C

1.0" Hose Crimp Chart

Measured Hose Wall Thickness Min. / Max.	Measured Hose OD Min. / Max.	Measured Hose OD In Closest 64ths	Finished Crimp Diameter Decimal	Finished Crimp Diameter Closest 64ths	Crimp Die	Setting	Dixon Sanitary Stainless Steel Crimp Ferrules
0.215 / 0.223	1.431 / 1.445	1 28/64	1.573	1 37/64	34	5.96	F16G-1500
0.223 / 0.230	1.446 / 1.461	1 29/64	1.585	1 37/64	34	6.25	F16G-1500
0.231 / 0.238	1.462 / 1.477	1 30/64	1.596	1 38/64	34	6.55	F16G-1500
0.239 / 0.246	1.478 / 1.492	1 31/64	1.608	1 39/64	34	6.84	F16G-1500
0.247 / 0.254	1.493 / 1.508	1 32/64	1.619	1 40/64	34	7.13	F16G-1547
0.254 / 0.262	1.509 / 1.523	1 33/64	1.631	1 40/64	34	7.43	F16G-1547
0.262 / 0.270	1.524 / 1.539	1 34/64	1.643	1 41/64	34	7.72	F16G-1547
0.270 / 0.277	1.540 / 1.555	1 35/64	1.654	1 42/64	34	8.02	F16G-1594
0.278 / 0.285	1.556 / 1.570	1 36/64	1.666	1 43/64	34	8.31	F16G-1594
0.286 / 0.293	1.571 / 1.586	1 37/64	1.677	1 43/64	34	8.60	F16G-1594

Note: Refer to Recommended Crimp Chart Index Selection to validate if you are using the appropriate chart for the hose on hand. This chart refers to Dixon Sanitary Style Crimp Stems.

Table F-C

1.5" Hose Crimp Chart

Measured Hose Wall Thickness Min. / Max.	Measured Hose OD Min. / Max.	Measured Hose OD In Closest 64ths	Finished Crimp Diameter Decimal	Finished Crimp Diameter Closest 64ths	Crimp Die	Setting	Dixon Sanitary Stainless Steel Crimp Ferrules
0.200 / 0.207	1.899 / 1.914	1 58/64	2.049	2 3/64	50	2.05	F24G-1969
0.208 / 0.215	1.915 / 1.930	1 59/64	2.061	2 4/64	50	2.35	F24G-1969
0.215 / 0.223	1.931 / 1.945	1 60/64	2.072	2 5/64	50	2.64	F24G-1969
0.223 / 0.230	1.946 / 1.961	1 61/64	2.084	2 5/64	50	2.93	F24G-1969
0.231 / 0.238	1.962 / 1.977	1 62/64	2.096	2 6/64	50	3.23	F24G-2031
0.239 / 0.246	1.978 / 1.992	1 63/64	2.107	2 7/64	50	3.52	F24G-2031
0.247 / 0.254	1.993 / 2.008	2	2.119	2 8/64	50	3.81	F24G-2031
0.254 / 0.262	2.009 / 2.023	2 1/64	2.130	2 8/64	50	4.11	F24G-2031
0.262 / 0.270	2.024 / 2.039	2 2/64	2.142	2 9/64	50	4.40	F24G-2094
0.270 / 0.277	2.040 / 2.055	2 3/64	2.153	2 10/64	50	4.70	F24G-2094
0.278 / 0.285	2.056 / 2.070	2 4/64	2.165	2 11/64	50	4.99	F24G-2094
0.286 / 0.293	2.071 / 2.086	2 5/64	2.177	2 11/64	50	5.28	F24G-2094
0.293 / 0.301	2.087 / 2.102	2 6/64	2.188	2 12/64	50	5.58	F24G-2156
0.301 / 0.309	2.103 / 2.117	2 7/64	2.200	2 13/64	50	5.87	F24G-2156
0.309 / 0.316	2.118 / 2.133	2 8/64	2.211	2 14/64	50	6.16	F24G-2156
0.317 / 0.324	2.134 / 2.148	2 9/64	2.223	2 14/64	50	6.16	F24G-2156

Note: Refer to Recommended Crimp Chart Index Selection to validate if you are using the appropriate chart for the hose on hand. This chart refers to Dixon Sanitary Style Crimp Stems.

Table F-C

2.0" Hose Crimp Chart

Measured Hose Wall Thickness Min. / Max.	Measured Hose OD Min. / Max.	Measured Hose OD In Closest 64ths	Finished Crimp Diameter Decimal	Finished Crimp Diameter Closest 64ths	Crimp Die	Setting	Dixon Sanitary Stainless Steel Crimp Ferrules
0.247 / 0.254	2.493 / 2.508	2 32/64	2.607	2 39/64	62	4.22	F32G-2594
0.254 / 0.262	2.509 / 2.523	2 33/64	2.618	2 40/64	62	4.50	F32G-2594
0.262 / 0.270	2.524 / 2.539	2 34/64	2.629	2 40/64	62	4.79	F32G-2594
0.270 / 0.277	2.540 / 2.555	2 35/64	2.641	2 41/64	62	5.07	F32G-2594
0.278 / 0.285	2.556 / 2.570	2 36/64	2.652	2 42/64	62	5.36	F32G-2594
0.286 / 0.293	2.571 / 2.586	2 37/64	2.663	2 42/64	62	5.64	F32G-2656
0.293 / 0.301	2.587 / 2.602	2 38/64	2.674	2 43/64	62	5.93	F32G-2656
0.301 / 0.309	2.603 / 2.617	2 39/64	2.686	2 44/64	62	6.22	F32G-2656
0.309 / 0.316	2.618 / 2.633	2 40/64	2.697	2 45/64	62	6.50	F32G-2656
0.317 / 0.324	2.634 / 2.648	2 41/64	2.708	2 45/64	62	6.79	F32G-2656
0.325 / 0.332	2.649 / 2.664	2 42/64	2.719	2 46/64	62	7.07	F32G-2719
0.333 / 0.340	2.665 / 2.680	2 43/64	2.731	2 47/64	62	7.36	F32G-2719
0.340 / 0.348	2.681 / 2.695	2 44/64	2.742	2 47/64	69	0.64	F32G-2719
0.348 / 0.355	2.696 / 2.711	2 45/64	2.753	2 48/64	69	0.93	F32G-2719
0.356 / 0.363	2.712 / 2.727	2 46/64	2.764	2 49/64	69	1.22	F32G-2875
0.364 / 0.371	2.728 / 2.742	2 47/64	2.776	2 50/64	69	1.50	F32G-2875

Note: Refer to Recommended Crimp Chart Index Selection to validate if you are using the appropriate chart for the hose on hand. This chart refers to Dixon Sanitary Style Crimp Stems.

Table F-C

2.5" Hose Crimp Chart

Measured Hose Wall Thickness Min. / Max.	Measured Hose OD Min. / Max.	Measured Hose OD In Closest 64ths	Finished Crimp Diameter Decimal	Finished Crimp Diameter Closest 64ths	Crimp Die	Setting	Dixon Sanitary Stainless Steel Crimp Ferrules
0.247 / 0.254	2.993 / 3.008	3	3.099	3 6/64	78	0.7	F40G-3063
0.254 / 0.262	3.009 / 3.023	3 1/64	3.109	3 7/64	78	1.0	F40G-3063
0.262 / 0.270	3.024 / 3.039	3 2/64	3.120	3 8/64	78	1.3	F40G-3063
0.270 / 0.277	3.040 / 3.055	3 3/64	3.131	3 8/64	78	1.5	F40G-3063
0.278 / 0.285	3.056 / 3.070	3 4/64	3.142	3 9/64	78	1.8	F40G-3125
0.286 / 0.293	3.071 / 3.086	3 5/64	3.153	3 10/64	78	2.1	F40G-3125
0.293 / 0.301	3.087 / 3.102	3 6/64	3.164	3 11/64	78	2.4	F40G-3125
0.301 / 0.309	3.103 / 3.117	3 7/64	3.175	3 11/64	78	2.6	F40G-3125
0.309 / 0.316	3.118 / 3.133	3 8/64	3.186	3 12/64	78	2.9	F40G-3188
0.317 / 0.324	3.134 / 3.148	3 9/64	3.197	3 13/64	78	3.2	F40G-3188
0.325 / 0.332	3.149 / 3.164	3 10/64	3.208	3 13/64	78	3.5	F40G-3188
0.333 / 0.340	3.165 / 3.180	3 11/64	3.219	3 14/64	78	3.8	F40G-3188
0.340 / 0.348	3.181 / 3.195	3 12/64	3.230	3 15/64	78	4.0	F40G-3250
0.348 / 0.355	3.196 / 3.211	3 13/64	3.241	3 15/64	78	4.3	F40G-3250
0.356 / 0.363	3.212 / 3.227	3 14/64	3.252	3 16/64	78	4.6	F40G-3250
0.364 / 0.371	3.228 / 3.242	3 15/64	3.263	3 17/64	78	4.9	F40G-3250

Note: Refer to Recommended Crimp Chart Index Selection to validate if you are using the appropriate chart for the hose on hand. This chart refers to Dixon Sanitary Style Crimp Stems.

Table F-C

3.0" Hose Crimp Chart

Measured Hose Wall Thickness Min. / Max.	Measured Hose OD Min. / Max.	Measured Hose OD In Closest 64ths	Finished Crimp Diameter Decimal	Finished Crimp Diameter Closest 64ths	Crimp Die	Setting	Dixon Sanitary Stainless Steel Crimp Ferrules
0.262 / 0.270	3.524 / 3.539	3 34/64	3.619	3 40/64	86	5.93	-
0.270 / 0.277	3.540 / 3.555	3 35/64	3.630	3 40/64	86	6.21	-
0.278 / 0.285	3.556 / 3.570	3 36/64	3.641	3 41/64	86	6.49	F48G-3625
0.286 / 0.293	3.571 / 3.586	3 37/64	3.652	3 42/64	86	6.77	F48G-3625
0.293 / 0.301	3.587 / 3.602	3 38/64	3.663	3 42/64	86	7.05	F48G-3625
0.301 / 0.309	3.603 / 3.617	3 39/64	3.674	3 43/64	86	7.32	F48G-3625
0.309 / 0.316	3.618 / 3.633	3 40/64	3.685	3 44/64	92	1.60	F48G-3688
0.317 / 0.324	3.634 / 3.648	3 41/64	3.696	3 45/64	92	1.88	F48G-3688
0.325 / 0.332	3.649 / 3.664	3 42/64	3.707	3 45/64	92	2.16	F48G-3688
0.333 / 0.340	3.665 / 3.680	3 43/64	3.718	3 46/64	92	2.43	F48G-3688
0.340 / 0.348	3.681 / 3.695	3 44/64	3.729	3 47/64	92	2.71	F48G-3750
0.348 / 0.355	3.696 / 3.711	3 45/64	3.740	3 47/64	92	2.99	F48G-3750
0.356 / 0.363	3.712 / 3.727	3 46/64	3.751	3 48/64	92	3.27	F48G-3750
0.364 / 0.371	3.728 / 3.742	3 47/64	3.762	3 49/64	92	3.55	F48G-3750

Note: Refer to Recommended Crimp Chart Index Selection to validate if you are using the appropriate chart for the hose on hand. This chart refers to Dixon Sanitary Style Crimp Stems.

Table F-D

2.0" Hose Crimp Chart

Measured Hose Wall Thickness Min. / Max.	Measured Hose OD Min. / Max.	Measured Hose OD In Closest 64ths	Finished Crimp Diameter Decimal	Finished Crimp Diameter Closest 64ths	Crimp Die	Setting	Dixon Sanitary Stainless Steel Crimp Ferrules
0.290	2.580	2 37/64	2.770	2 49/64	69	1.4	F32G-2656
0.300	2.600	2 38/64	2.790	2 50/64	69	1.8	F32G-2656
0.310	2.620	2 40/64	2.800	2 51/64	69	2.2	F32G-2656
0.320	2.640	2 41/64	2.820	2 52/64	69	2.6	F32G-2719
0.330	2.660	2 42/64	2.830	2 53/64	69	2.9	F32G-2719
0.340	2.680	2 44/64	2.850	2 54/64	69	3.3	F32G-2719
0.350	2.700	2 45/64	2.860	2 55/64	69	3.7	F32G-2719
0.360	2.720	2 46/64	2.880	2 56/64	69	4.1	F32G-2875
0.370	2.740	2 47/64	2.900	2 56/64	69	4.5	F32G-2875
0.380	2.760	2 49/64	2.910	2 58/64	69	4.8	F32G-2875
0.390	2.780	2 50/64	2.920	2 59/64	69	5.2	F32G-2875

Refer to assembly instructions to use banding coil.


Note: A hose pusher is required for coupling insertion.

Refer to Recommended Crimp Chart Index Selection to validate if you are using the appropriate chart for the hose on hand.

This chart refers to Dixon Sanitary Style Crimp Stems.

Continental Vintner Reserve 250 CB/ 250 EPDM

Fitting: 20PCTFC50X / 20PCTMC50X

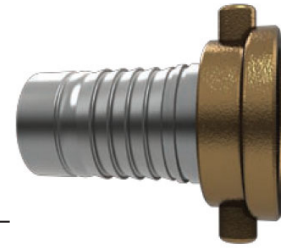


2.0" Hose Crimp Chart

By Hose Wall Thickness				By Hose OD				PT Sanitary Crimp Diameter				Ferrule		
Min		Max		Min		Max		Closest 64th	Diameter (Decimals)	Closest 64th	Crimp Die		Setting	
(in.)	(mm)	(in.)	(mm)	(in.)	(mm)	(in.)	(mm)							
0.200	0.207	5.1	5.3	2.399	2.414	60.9	61.3	2 26/64	2.569	65.3	2 36/64	62	3.25	20216 SFC50P
0.208	0.215	5.3	5.5	2.415	2.430	61.3	61.7	2 27/64	2.582	65.6	2 37/64	62	3.57	
0.215	0.223	5.5	5.7	2.431	2.445	61.7	62.1	2 28/64	2.594	65.9	2 38/64	62	3.89	
0.223	0.230	5.7	5.9	2.446	2.461	62.1	62.5	2 29/64	2.607	66.2	2 39/64	62	4.21	20218 SFC50P
0.231	0.238	5.9	6.1	2.462	2.477	62.5	62.9	2 30/64	2.619	66.5	2 40/64	62	4.52	
0.239	0.246	6.1	6.3	2.478	2.492	62.9	63.3	2 31/64	2.632	66.8	2 40/64	62	4.84	
0.247	0.254	6.3	6.4	2.493	2.508	63.3	63.7	2 32/64	2.644	67.2	2 41/64	62	5.16	20220 SFC50P
0.254	0.262	6.5	6.6	2.509	2.523	63.7	64.1	2 33/64	2.657	67.5	2 42/64	62	5.48	
0.262	0.270	6.7	6.8	2.524	2.539	64.1	64.5	2 34/64	2.669	67.8	2 43/64	62	5.79	
0.270	0.277	6.9	7.0	2.540	2.555	64.5	64.9	2 35/64	2.682	68.1	2 44/64	62	6.11	20222 SFC50P
0.278	0.285	7.1	7.2	2.556	2.570	64.9	65.3	2 36/64	2.694	68.4	2 44/64	62	6.43	
0.286	0.293	7.3	7.4	2.571	2.586	65.3	65.7	2 37/64	2.707	68.7	2 45/64	62	6.75	
0.293	0.301	7.5	7.6	2.587	2.602	65.7	66.1	2 38/64	2.719	69.1	2 46/64	62	7.06	20224 SFC50P
0.301	0.309	7.7	7.8	2.603	2.617	66.1	66.5	2 39/64	2.732	69.4	2 47/64	62	7.38	
0.309	0.316	7.9	8.0	2.618	2.633	66.5	66.9	2 40/64	2.744	69.7	2 48/64	62	7.70	
0.317	0.324	8.0	8.2	2.634	2.648	66.9	67.3	2 41/64	2.757	70.0	2 48/64	62	8.02	20226 SFC50P
0.325	0.332	8.2	8.4	2.649	2.664	67.3	67.7	2 42/64	2.769	70.3	2 49/64	62	1.33	
0.333	0.340	8.4	8.6	2.665	2.680	67.7	68.1	2 43/64	2.782	70.7	2 50/64	62	1.65	
0.340	0.348	8.6	8.8	2.681	2.695	68.1	68.5	2 44/64	2.794	71.0	2 51/64	62	1.97	20228 SFC50P
0.348	0.355	8.8	9.0	2.696	2.711	68.5	68.9	2 45/64	2.807	71.3	2 52/64	62	2.29	
0.356	0.363	9.0	9.2	2.712	2.727	68.9	69.3	2 46/64	2.819	71.6	2 52/64	69	2.60	
0.364	0.371	9.2	9.4	2.728	2.742	69.3	69.7	2 47/64	2.832	71.9	2 53/64	69	2.92	20230 SFC50P
0.372	0.379	9.4	9.6	2.743	2.758	69.7	70.0	2 48/64	2.844	72.2	2 54/64	69	3.24	
0.379	0.387	9.6	9.8	2.759	2.773	70.1	70.4	2 49/64	2.857	72.6	2 55/64	69	3.56	
0.387	0.395	9.8	10.0	2.774	2.789	70.5	70.8	2 50/64	2.869	72.9	2 56/64	69	3.87	20230 SFC50P
0.395	0.402	10.0	10.2	2.790	2.805	70.9	71.2	2 51/64	2.882	73.2	2 56/64	69	4.19	
0.403	0.410	10.2	10.4	2.806	2.820	71.3	71.6	2 52/64	2.894	73.5	2 57/64	69	4.51	
0.411	0.418	10.4	10.6	2.821	2.836	71.7	72.0	2 53/64	2.907	73.8	2 58/64	69	4.83	

Continental Vintner Reserve 250 CB/ 250 EPDM

Fitting: 30PCTFC50X / 30PCTMC50X

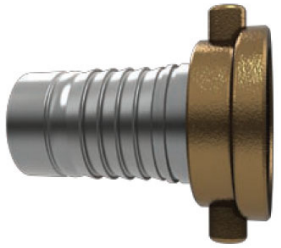

3.0" Hose Crimp Chart

By Hose Wall Thickness				By Hose OD				PT Sanitary Crimp Diameter				Ferrule		
Min		Max		Min		Max		Closest 64th	Diameter (Decimals)	Closest 64th	Crimp Die		Setting	
(in.)	(mm)	(in.)	(mm)	(in.)	(mm)	(in.)	(mm)							
0.200	0.207	5.1	5.3	3.399	3.414	86.3	86.7	3 26/64	3.601	91.5	3 38/64	86	5.47	20216 SFC50P
0.208	0.215	5.3	5.5	3.415	3.430	86.7	87.1	3 27/64	3.614	91.8	3 39/64	86	5.78	
0.215	0.223	5.5	5.7	3.431	3.445	87.1	87.5	3 28/64	3.626	92.1	3 40/64	86	6.10	
0.223	0.230	5.7	5.9	3.446	3.461	87.5	87.9	3 29/64	3.639	92.4	3 41/64	86	6.42	20218 SFC50P
0.231	0.238	5.9	6.1	3.462	3.477	87.9	88.3	3 30/64	3.651	92.7	3 42/64	86	6.74	
0.239	0.246	6.1	6.3	3.478	3.492	88.3	88.7	3 31/64	3.664	93.1	3 42/64	86	7.05	
0.247	0.254	6.3	6.4	3.493	3.508	88.7	89.1	3 32/64	3.676	93.4	3 43/64	86	7.37	20220 SFC50P
0.254	0.262	6.5	6.6	3.509	3.523	89.1	89.5	3 33/64	3.689	93.7	3 44/64	86	7.69	
0.262	0.270	6.7	6.8	3.524	3.539	89.5	89.9	3 34/64	3.701	94.0	3 45/64	86	8.01	
0.270	0.277	6.9	7.0	3.540	3.555	89.9	90.3	3 35/64	3.714	94.3	3 46/64	92	2.32	20222 SFC50P
0.278	0.285	7.1	7.2	3.556	3.570	90.3	90.7	3 36/64	3.726	94.6	3 46/64	92	2.64	
0.286	0.293	7.3	7.4	3.571	3.586	90.7	91.1	3 37/64	3.739	95.0	3 47/64	92	2.96	
0.293	0.301	7.5	7.6	3.587	3.602	91.1	91.5	3 38/64	3.751	95.3	3 48/64	92	3.28	20224 SFC50P
0.301	0.309	7.7	7.8	3.603	3.617	91.5	91.9	3 39/64	3.764	95.6	3 49/64	92	3.59	
0.309	0.316	7.9	8.0	3.618	3.633	91.9	92.3	3 40/64	3.776	95.9	3 50/64	92	3.91	
0.317	0.324	8.0	8.2	3.634	3.648	92.3	92.7	3 41/64	3.789	96.2	3 50/64	92	4.23	20226 SFC50P
0.325	0.332	8.2	8.4	3.649	3.664	92.7	93.1	3 42/64	3.801	96.5	3 51/64	92	4.55	
0.333	0.340	8.4	8.6	3.665	3.680	93.1	93.5	3 43/64	3.814	96.9	3 52/64	92	4.86	
0.340	0.348	8.6	8.8	3.681	3.695	93.5	93.9	3 44/64	3.826	97.2	3 53/64	92	5.18	20228 SFC50P
0.348	0.355	8.8	9.0	3.696	3.711	93.9	94.3	3 45/64	3.839	97.5	3 54/64	92	5.50	
0.356	0.363	9.0	9.2	3.712	3.727	94.3	94.7	3 46/64	3.851	97.8	3 54/64	92	5.82	
0.364	0.371	9.2	9.4	3.728	3.742	94.7	95.1	3 47/64	3.864	98.1	3 55/64	92	6.13	20230 SFC50P
0.372	0.379	9.4	9.6	3.743	3.758	95.1	95.4	3 48/64	3.876	98.5	3 56/64	92	6.45	
0.379	0.387	9.6	9.8	3.759	3.773	95.5	95.8	3 49/64	3.889	98.8	3 57/64	92	6.77	
0.387	0.395	9.8	10.0	3.774	3.789	95.9	96.2	3 50/64	3.901	99.1	3 58/64	92	7.09	20230 SFC50P
0.395	0.402	10.0	10.2	3.790	3.805	96.3	96.6	3 51/64	3.914	99.4	3 58/64	92	7.40	
0.403	0.410	10.2	10.4	3.806	3.820	96.7	97.0	3 52/64	3.926	99.7	3 59/64	92	7.72	
0.411	0.418	10.4	10.6	3.821	3.836	97.1	97.4	3 53/64	3.939	100.0	3 60/64	92	8.04	20230 SFC50P
0.418	0.426	10.6	10.8	3.837	3.852	97.5	97.8	3 54/64	3.951	100.4	3 61/64	92	8.36	
0.426	0.434	10.8	11.0	3.853	3.867	97.9	98.2	3 55/64	3.964	100.7	3 62/64	92	8.67	
0.434	0.441	11.0	11.2	3.868	3.883	98.3	98.6	3 56/64	3.976	101.0	3 62/64	92	8.99	20230 SFC50P
0.442	0.449	11.2	11.4	3.884	3.898	98.6	99.0	3 57/64	3.989	101.3	3 63/64	92	9.31	
0.450	0.457	11.4	11.6	3.899	3.914	99.0	99.4	3 58/64	4.001	101.6	4	92	9.63	

Appendix

Assembly Instructions for Hose with PVC Helix in the Cover

1. Using a caliper, measure the hose wall thickness in 4 locations before applying the banding coil, then calculate the average wall thickness.

Banding coil is mainly used to fill the gap between the PVC helices on the cover and to help seal the tube at the tip of the nipple. Use the dedicated transparent banding coils.

2. Slide the ferrule temporarily over the hose end, and mark the finish location of the ferrule on the hose.



3. Put the required number of turns of the banding coils under the ferrule position, insert the ferrule and leave about 1" of banding coil past the ferrule edge.

4. Insert the stem, validate the final position of the ferrule and crimp according to crimp chart.

Part Numbers:

21005556 BANDING COIL POLY ROD for EZ GLIDE WINE ID 1.5" and 2" X 5'

21005557 BANDING COIL POLY ROD for EZ GLIDE WINE ID 3 » X5'

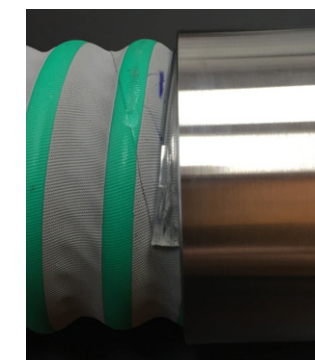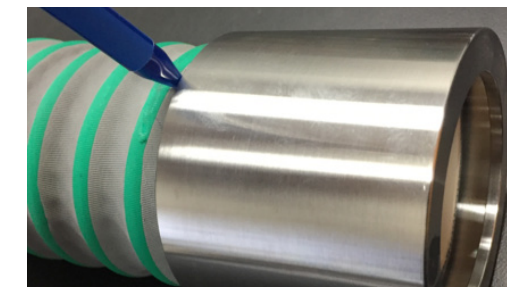

Instructions for Replacing Handles, Pins and Rings on Insta-Lock™ Fittings

Before replacing the handles on an Insta-Lock™ fitting, examine the fitting for external damage. Some things to look for: the bowl on a "B, C, or D" type being out of round, damage to the hose shank barb, cracks in the casting, or general wear and abuse. If you find any damage or question the integrity of the fitting, immediately discard the fitting.

To remove the handles, locate the end of the pin with the notches. With a drift pin and a hammer, drive the pin out from the casting by driving the pin from the un-notched side toward the notched side. The pin can only be correctly removed and installed this way.

Reverse the above procedure to install the new handle and pin and pull ring. Ensure the pin is inserted completely and flush with the casting.

Always use all the parts in a kit.

Always replace both handles, pins and pull rings.

Always replace the gasket with the appropriate gasket for the service required.

Always use appropriate safety glasses.

Hose Testing Methods

Safety Warning!

Testing can be dangerous and should be done only by trained personnel using proper tools and procedures. Failure to follow such procedures might result in damage to property and/or serious bodily injury.

The Association of Rubber Product Manufacturers (ARPM) recognizes, accepts and recommends the testing methods of the American Society for Testing and Materials (ASTM).

Unless otherwise specified, all hose tests are to be conducted in accordance with ASTM Method No. D-380 (latest revision). Where an ASTM D-380 test is not available, another test method should be selected and described in detail.

ARPM participates with ASTM under the auspices of the American National Standards Institute (ANSI) in Technical Committee 45 (TC45) of The International Organization for Standardization (ISO) in developing both hose product and hose test method standards. Many of the hose test method standards published by ISO duplicate or closely parallel those shown in ASTM D-380. Many are unique and, in those cases, the RMA may be able to provide the necessary test standard references, which may be purchased from the American National Standards Institute (ANSI).

Hydrostatic Pressure Tests

Hydrostatic pressure tests are classified as follows:

1. Destructive Type
 - a. Burst test
 - b. Hold test
2. Non-Destructive Type
 - a. Proof pressure test
 - b. Change in length test (elongation or contraction)
 - c. Change in outside diameter or circumference test
 - d. Warp test
 - e. Rise test
 - f. Twist test
 - g. Kink test
 - h. Volumetric expansion test

Destructive Tests

Destructive tests are conducted on short specimens of hose, normally 18 inches (460mm) to 36 inches (915 mm) in length and, as the name implies, the hose is destroyed in the performance of the test.

- a. Burst pressure is recorded as the pressure at which actual rupture of a hose occurs.
- b. A hold test, when required, is a means of determining whether weakness will develop under a given pressure for a specified period of time.

(Printing under permission by ARPM)

© 2015 by the Association of Rubber Product Manufacturers. All rights reserved.
Association of Rubber Product Manufacturers • 1400 K Street, NW • Washington, D.C. 20005 • 202.682.4800 • 202.682.4854

spiral) and that at the proof pressure times 100 divided by the length at 10 psi (0.069 MPa). Elongation occurs if the length of the hose under the proof pressure is greater than at a pressure of 10 psi (0.069 MPa). Contraction occurs if the length at the proof pressure is less than at 10 psi (0.069 MPa). In testing wire braided or spiralled hose, the proof pressure is applied and the length recorded. The pressure is then released and, at the end of 30 seconds, the length is measured; the measurement obtained is termed the "original length."

- c. Percent change in outside diameter or circumference is the difference between the outside diameter or circumference at 10 psi (0.069 MPa) and that obtained under the proof pressure times 100 divided by the outside diameter or circumference at 10 psi (0.069 MPa). Expansion occurs if the measurement at the proof pressure is greater than at 10 psi (0.069 MPa). Contraction occurs if the measurement at the proof pressure is less than at 10 psi (0.069 MPa).
- d. Warp is the deviation from a straight line drawn from fitting to fitting; the maximum deviation from this line is warp. First, a measurement is taken at 10 psi (0.069 MPa) and then again at the proof pressure. The difference between the two, in inches, is the warp. Normally this is a feature measured on woven jacket fire hose only.
- e. Rise is a measure of the height a hose rises from the surface of the test table while under pressure. The difference between the rise at 10 psi (0.069 MPa) and at the proof pressure is reported to the nearest 0.25 inch (6.4 mm). Normally, this is a feature measured on woven jacket fire hose only.
- f. Twist is a rotation of the free end of the hose while under pressure. A first reading is taken at 10 psi (0.069 MPa) and a second reading at proof pressure. The difference, in degrees, between the 10 psi (0.069 MPa) base and that at the proof pressure is the twist. Twist is reported as right twist (to tighten couplings) or left twist. Standing at the pressure inlet and looking toward the free end of a hose, a clockwise turning is right twist and counterclockwise is left twist.
- g. Kink test is a measure of the ability of woven jacket hose to withstand a momentary pressure while the hose is bent back sharply on itself at a point approximately 18 inches (457mm) from one end. Test is made at pressures ranging from 62% of the proof pressure on sizes 3 inches (76mm) and 3.5 inches (89mm) to 87% on sizes under 3 inches (76mm). This is a test applied to woven jacket fire hose only.
- h. Volumetric expansion test is applicable only to specific types of hose, such as hydraulic or power steering hose, and is a measure of its volumetric expansion under ranges of internal pressure.

(Printing under permission by ARPM)

© 2015 by the Association of Rubber Product Manufacturers Association. All rights reserved.
Association of Rubber Product Manufacturers • 1400 K Street, NW • Washington, D.C. 20005 • 202.682.4800 • 202.682.4854

Design Considerations

In designing hose, it is customary to develop a design ratio, which is a ratio between the minimum burst and the maximum working pressure.

Burst test data is compiled and the minimum value is established by accepted statistical techniques. This is done as a check on theoretical calculations, based on the strength of reinforcing materials and on the characteristics of the method of fabrication.

Minimum burst values are used as one factor in the establishment of a reasonable and safe maximum working pressure.

MAXIMUM WORKING PRESSURE IS ONE OF THE ESSENTIAL OPERATING CHARACTERISTICS THAT A HOSE USER MUST KNOW AND RESPECT TO ASSURE SATISFACTORY SERVICE AND OPTIMUM LIFE.

It should be noted that design ratios are dependent on more than the minimum burst. The hose technologist must anticipate natural decay in strength of reinforcing materials, and the accelerated decay induced by the anticipated environments in which the hose will be used and the dynamic situations that a hose might likely encounter in service. Including all considerations, the following recommended design ratios are given for newly manufactured hose:

1. Water Hose up to 150 psi WP: 3:1
2. Hose for all other liquids, solid materials suspended in liquids or air, and water hose over 150 psi WP: 4:1
3. Hose for compressed air and other gases: 4:1
4. Hose for liquid media that immediately changes into gas under standard atmospheric conditions: 5:1
5. Steam Hose: 10:1

Electrical Resistance Tests For Hose and Hose Assemblies

1.0 Purpose: This procedure specifies methods for performing electrical resistance tests on rubber and/or plastic hose and hose assemblies.

2.0 Scope: These procedures are intended to test electrical conductive, antistatic and nonconductive (insulating) hoses, along with electrical continuity or discontinuity between fittings.

3.0 Definitions

3.1 Antistatic Hose - Antistatic hose constructions are those that are capable of dissipating the static electricity buildup that occurs during the high velocity flow of material through a hose.

3.2 Conductive Hose - Conductive hose constructions are those that are capable of conducting an electrical current.

3.3 Direct Current (D.C.): Flow of electrical current in one direction at a constant rate.

3.4 Electrical Conductivity: A measure of the ease with which a material is capable of conducting an electrical current. Conductivity = $1/\text{Resistance}$.

3.5 Electrical Resistance: Property of an object to resist or oppose the flow of an electrical current.

3.6 Non-Conductive (Insulating) Hose: Non-conductive hose constructions are those that resist the flow of electrical current.

3.7 Ohm's Law: The electrical current, I, is equal to the applied voltage, V, divided by the resistance, R. In practical terms, the higher the electrical resistance at a constant voltage, the lower the electrical current flow through an object.

3.8 Ohm: The amount of resistance that limits the passage of current to one ampere when a voltage of one volt is applied to it.

4.0 Apparatus

4.1 Test Instruments

All test instruments shall have a gauge reliability and

reproducibility (R&R) of less than 30%. Some instruments made to measure high electrical resistance may have an internal protection circuit built in which will cause test errors in the less than one megohm range. During the test, no more than 3 watts (W) shall be dissipated in the specimen, to prevent erroneous results due to effects of temperature.

The power dissipated shall be determined by the square of the open-circuit voltage divided by the measured resistance, see formula 1 (Power Dissipation).

$$1) \text{ Power Dissipation} = \frac{(\text{Voltage})^2}{\text{Resistance in ohms}}$$

To determine the electrical resistance of non-conductive hose, the test should be made with an instrument designed specifically for measuring insulation resistance, having a nominal open-circuit voltage of 500 volts D.C., or with any other instrument known to give comparable results. For measuring electrical discontinuity, a 1,000 Volt D.C. source may be used instead of a 500 volt D.C. source.

For hoses with a conductive tube or cover, the resistance values obtained may vary with the applied voltage, and errors may occur at low-test voltages. As a starting point, an ohmmeter (9 volts) can be used.

For tests requiring measurement of electrical continuity between end fittings or through continuous internal or external bonded wires, the instrument used shall be an ohmmeter (9 volts).

4.2 Electrodes and Contacts

When the test procedure calls for contact with the hose cover, electrodes shall be formed around the outer circumference of the hose as bands 25mm +2mm, 0mm (1 in. +1/16 in., 0 in.) wide by applying silver lacquer/conductive liquid and metallic copper foil tape (i.e. 3M Scotch Brand) as shown in Figure 1.

When a conductive silver lacquer (i.e. Colloidal Silver Liquid is available from Ted Pella, Inc. catalogue # 16031) is used, the surface resistance between any two points on a sample of the dried film shall not exceed 100 Ω .

(Printing under permission by ARPM)

© 2015 by the Association of Rubber Product Manufacturers. All rights reserved.
Association of Rubber Product Manufacturers • 1400 K Street, NW • Washington, D.C. 20005 • 202.682.4800 • 202.682.4854

When a conductive liquid is used the electrode contact area shall be completely wetted and shall remain so until the end of the test. The conductive liquid shall consist of:

- Anhydrous polyethylene glycol of relative molecular mass 600: 800 parts by mass
- Water: 200 parts by mass
- Wetting agent: 1 part by mass
- Potassium Chloride: 10 parts by mass

When the test procedure calls for contact with the hose tube, it is preferable to use a copper plug of external diameter equal to or slightly greater than the hose ID or a steel hose stem, coated with the conducting liquid, and pushed 25 mm (1 in.) into the hose. An alternative for 50 mm (2 in.) and above hose would be to apply the conductive silver lacquer onto the hose ID, then insert the plug or hose stem. The electrical leads from the test instrument shall be clean and they should make adequate contact with the metallic copper foil and/or copper plugs/hose stems.

5.0 Preparation and Cleaning for Test

The surfaces of the hose shall be clean. If necessary, the hose surface may be cleaned by rubbing with Fuller's earth (magnesium aluminum silicate) and water, followed by a distilled water rinse, and allowing the hose to dry in a non-contaminating environment. Do not use organic materials that attack or swell the rubber, and do not buff or abrade the test surfaces.

The surface of the hose shall not be deformed either during the application of the contacts or during the test. When using test pieces, the supports shall be outside the test length. When using a long length of hose, the hose shall be uncoiled and laid out straight on polyethylene or other suitable insulating material. Care should be taken to ensure that the hose is insulated from any electrical leakage path along the length of the hose.

6.0 Test Conditions

For lab testing, the hose or hose assemblies shall be conditioned for at least 16 hours at $+23^{\circ}\text{C} \pm 2^{\circ}\text{C}$ ($73.4^{\circ}\text{F} \pm 3.6^{\circ}\text{F}$) with a relative humidity not to exceed 70%. However, it is permissible, by agreement between the supplier and the customer, to use the conditions prevailing in the factory, warehouse, or laboratory, provided that the relative humidity does not exceed 70%.

7.0 Test Pieces:

Prepare three test pieces approximately 300mm (12 in.) long from samples taken at random from a production run or lot. Condition the test pieces per section 6.0. Place the test piece on blocks of polyethylene, or other insulating material, to provide a resistance of greater than 1011 Ω between the test piece and the surface on which the blocks are supported. Ensure that the leads from the

(Printing under permission by ARPM)

© 2015 by the Association of Rubber Product Manufacturers. All rights reserved.
Association of Rubber Product Manufacturers • 1400 K Street, NW • Washington, D.C. 20005 • 202.682.4800 • 202.682.4854

instrument do not touch each other, the hose or any part except the terminal to which each is connected. Avoid breathing on the test surfaces and thus creating condensation that may lead to inaccuracies.

8.0 Procedure for hoses with conducting tube:

Apply the electrodes as specified to the inside surface of the hose at each end of the hose. The edge of the electrode plug shall be coincident with the end of the hose. When using a conductive liquid, care shall be taken to avoid creating a leakage path between the tube and the reinforcement or cover of the hose.

Apply the metal contacts to the electrodes.

Apply the test voltage (9V) and measure the resistance 5 seconds \pm 1 second after the voltage is applied.

Note: In previous editions of the hose handbook, this method was referred to as the Plug Method.

9.0 Procedure for hose with conducting cover

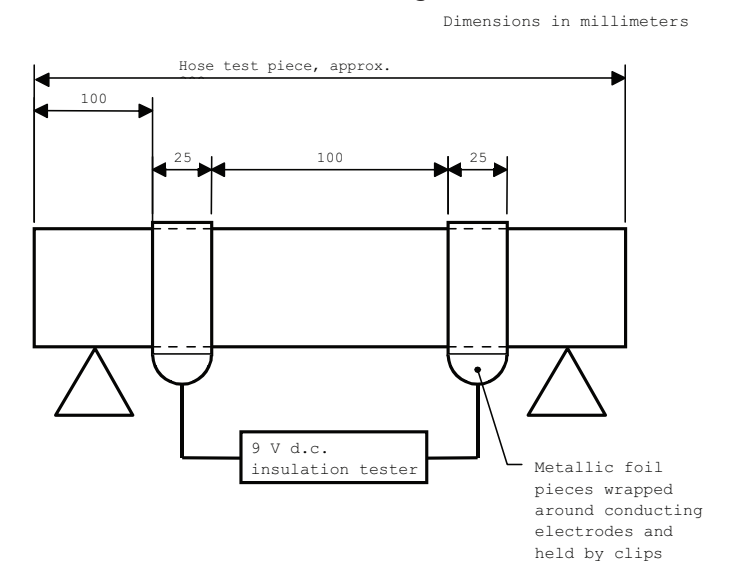


Figure 6-1 - Electrodes and contacts for testing hose

Apply the electrodes as specified to the outer circumference of the hose at each hose end. See Figure 6-1. Ensure that contact is maintained with the electrodes around the circumference and that the contact pieces are sufficiently long enough for the two free ends to be held securely by a tensioning clip (see Figure 6-1) such that the fit of the electrodes is as tight as possible.

(Printing under permission by ARPM)

© 2015 by the Association of Rubber Product Manufacturers. All rights reserved.
Association of Rubber Product Manufacturers • 1400 K Street, NW • Washington, D.C. 20005 • 202.682.4800 • 202.682.4854

Apply the metal contacts.

Apply the test voltage (9V) and measure the resistance 5 seconds \pm 1 second after the voltage is applied.

10.0 Procedure for hose with conducting or non-conducting compounds throughout

Apply the electrodes as specified on the inside surface at one end of the hose (end A) and on the outside surface at the other end of the hose (end B).

Apply the metal contacts to the electrodes.

Apply the test voltage (9V for conductive compounds and 500V for non-conductive compounds) and measure the resistance 5 seconds \pm 1 second after the voltage is applied.

Alternative method for non-conductive hose - Nail or "Pot Room" Method

Conduct test as follows:

1. Cut sample hose, 24 inches long
2. Assure that both inside and outside of hose are free of oil, dirt, etc.
3. Pierce sample ends with clean nails, as shown in Fig. 6-2.

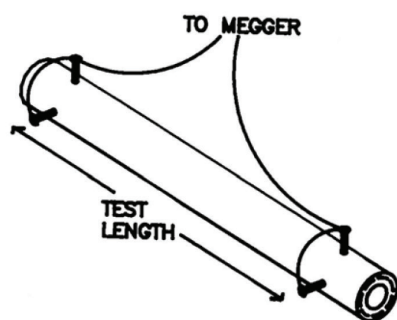


Fig. 6-2 - Nail or "Pot Room" Test

4. Connect nails to 1000-volt DC power source and megohm meter or 1000 volt "megger" as shown in Fig. 6-2.
5. Record total resistance, in megohms.
6. Measure "test length" as shown in Fig. 6-2.
7. Divide total resistance by test length to get megohms per inch.

11.0 Procedure for hose assemblies fitted with metal end fittings:

When it is required that the resistance of a hose assembly be measured, the leads of the test instrument shall be attached directly to the metal hose shank (threaded end connection, fixed flange, stub end of a floating flange, etc.) of the metal end fittings.

Some hoses, especially thermoplastic hoses, have conductive layers within the hose construction. These hoses shall be tested as assemblies made with fittings and assembly techniques specified by the hose and fitting manufacturer.

Apply the metal contacts to the metal end fittings.

Apply the test voltage (9V) and measure the resistance 5 seconds \pm 1 second after the voltage is applied.

12.0 Procedure for measurement of electrical continuity:

In certain types of hose constructions, electrical continuity is provided between the end fittings by means of a continuous wire or wires bonded to each coupling. When the construction is such that there are internal and external wires, the electrical continuity of both wires shall be established. It is essential that contact resistance between the end fittings and the ohmmeter be minimized.

Apply the metal contacts to the metal end fittings.

Apply the test voltage (9V) and measure the resistance 5 seconds \pm 1 second after the voltage is applied.

Velocity® Crimp Instructions

Notes

The Velocity® crimp specifications given are valid only for combination nipples, domestic suction couplings, ball and socket couplings, and the corresponding sleeves from Campbell Fittings, Inc. of Boyertown, PA, USA.

The crimp specifications in the charts are from Campbell Fittings with the following modification: The wall sizes are lined up with the proper crimp diameter for Velocity® hose. If you are using Campbell's published crimp specification guide you must follow the suggestions for hoses with a PVC outer helix, that is, to move up one row for the crimp diameter.

Banding coils are necessary to assure a leak-free connection.

Instructions

(The following instructions are excerpted from Campbell's crimp specification guide.)

To determine the sleeve choice and crimp specification:

1. Install the banding coil.
2. Measure each end to be assembled, as hoses may vary from end to end.
3. Determine the hose wall thickness by measuring 3 separate locations on the hose end with a caliper, add them together and divide by 3. Measurements should be taken over the helix and banding coil.
4. On the chart locate the wall thickness closest to the average measured hose wall. Read across for the sleeve and crimp diameter.

NOTE 1: If the recommended sleeve is too tight, the hose ID is oversized. Measure the hose OD and use the recommended sleeve based on the OD. However, crimp to the diameter specified based on the hose wall thickness (step 3).

NOTE 2: When multiple crimp hits are needed, turn the assembly for each hit for best results.

Safety Note

All assemblies should be hydrostatically tested to a minimum of 2 times the assembly working pressure or as otherwise dictated by Veyance, NAHAD Assembly Guidelines, or your customer. Always refer to the NAHAD Assembly Guidelines for industry-accepted practices for assembling hose and hydrostatic testing.

Suggestions For Preparing The Assembly

1. Prior to assembly assure that the sleeve and hose end is clean. Assure the hose end has been cut squarely.
2. Generally for PVC hose, it is recommended to soak both the fitting and hose in hot water prior to inserting the fitting. Velocity hose is rated to 140°F. About half an hour in 140°F water should work well. Generally, no pounding or hammering is required, only force and perhaps a screwing motion as if screwing the PVC helix wire onto the fitting.
3. Lubrication is not recommended unless necessary. If lubrication is necessary for fitting/coupling insertion, a commercial hose lube is recommended.
4. Do not crimp the assembly while still hot. Allow the fitting and hose to cool to room temperature or about 70°F before crimping. Proof testing is recommended.

Positioning

1. The fitting/coupling should be inserted into the hose only as far as to cover the last serration. Insertion beyond that point does not enhance retention, but may harm the fitting/coupling or interlock.
2. Sleeves should be positioned so the end of the sleeve and the end of the hose are aligned.
3. When crimping, the dies should align over the end of the sleeve on the coupling side. The entire length of the sleeve should be crimped. If dies are too short, crimp the fitting/coupling end first, then the end toward the hose length.

ARPM Hose Care Inspection Procedures

Hose has a limited life and the user must be alert to signs of impending failure, particularly when the conditions of service include high working pressures and/or the conveyance or containment of hazardous materials. The periodic inspection and testing procedures described here provide a schedule of specific measures which constitute a minimum level of user action to detect signs indicating hose deterioration or loss of performance before conditions leading to malfunction or failure are reached.

Safety Warning!

Failure to properly follow the manufacturer's recommended procedures for the care, maintenance and storage of a particular hose might result in its failure to perform in the manner intended and might result in possible damage to property and serious bodily injury.

General instructions are also described for the proper care of hose to minimize deterioration from exposure to elements or environments which are known to be deleterious to rubber products. Proper storage conditions can enhance and extend substantially the ultimate life of hose products.

General Care and Maintenance

Hose should not be subjected to any form of abuse in service. It should be handled with reasonable care. Hose should not be dragged over sharp or abrasive surfaces unless specifically designed for such service. Care should be taken to protect hose from severe end loads for which the hose or hose assembly were not designed. Hose should be used at or below its rated working pressure; any changes in pressure should be made gradually so as to not subject the hose to excessive surge pressures.

Hose should not be kinked or be run over by equipment. In handling large size hose, dollies should be used whenever possible; slings or handling rigs, properly placed, should be used to support heavy hose used in oil suction and discharge service.

General Test & Inspection Procedures

An inspection and hydrostatic test should be made at periodic intervals to determine if a hose is suitable for continued service. A visual inspection of the hose should be made for loose covers, kinks, bulges or soft spots, which might indicate broken or displaced reinforcement. The couplings or fittings should be closely examined and, if there is any sign of movement of the hose from the couplings, the hose should be removed from service.

The periodic inspection should include a hydrostatic test for one minute at 150% of the recommended working pressure of the hose. An exception to this would be the woven jacketed fire hose.* During the hydrostatic test, the hose should be straight, not coiled or in a kinked position. Water is the usual test medium and, following the test, the hose may be flushed with alcohol to remove traces of moisture. A regular schedule for testing should be followed and inspection records maintained.

Safety Warning: Before conducting any pressure tests on hose, provisions must be made to ensure the safety of the personnel performing the tests and to prevent any possible damage to property. Only trained personnel using proper tools and procedures should conduct any pressure tests.

- Air or any other compressible gas must never be used as the test media because of the explosive action of the hose should a failure occur. Such a failure might result in possible damage to property and serious bodily injury.
 - Air should be removed from the hose by bleeding it through an outlet valve while the hose is being filled with the test medium.
 - Hose to be pressure tested must be restrained by placing steel rods or straps close to each end and at approximate 10 foot (3m) intervals along its length to keep the hose from "whipping." If failure occurs, the steel rods or straps are to be anchored firmly to the test structure, but in such a manner that they do not contact the hose which must be free to move.
 - The outlet end of the hose is to be bulwarked so that a blown-out fitting will be stopped.
 - Provisions must be made to protect testing personnel from the forces of the pressure media if a failure occurs.
 - Testing personnel must never stand in front of or in back of the ends of a hose being pressure tested.
 - Testing personnel must never stand in front of or in back of the ends of a hose being pressure tested.
 - When liquids such as gasoline, oil, solvent or other hazardous fluids are used as the test fluid, precautions must be taken to protect against fire or other damage should a hose fail and the test liquid be sprayed over the surrounding area.
- The Rubber Manufacturers Association has published separately a series of Hose Technical Information bulletins describing Maintenance, Testing and Inspection recommendations. Reference should be made to the current RMA Catalog of Publications to determine the availability of the latest edition. Bulletins published as of January 1996 include the following:
- Publication Number
 IP 11-1-Steam Hose
 IP 11-2-Anhydrous Ammonia Hose
 IP 11-4-Oil Suction and Discharge Hose
 IP 11-5-Welding Hose
 IP 11-7-Chemical Hose
 IP 11-8-Fuel Dispensing Hose

Continued on next page

(Printing under permission by ARPM)

© 2015 by the Association of Rubber Product Manufacturers. All rights reserved.
 Association of Rubber Product Manufacturers • 1400 K Street, NW • Washington, D.C. 20005 • 202.682.4800 • 202.682.4854

*Woven jacket fire hose should be tested in accordance with the service test provisions contained in the current edition of National Fire Protection Association Bulletin No. 1962 - Standard for the Care, Use and Service Testing of Fire Hose.

